



U.S. Department
of Transportation
**National Highway
Traffic Safety
Administration**



DOT HS 811 094

March 2009

The Effects of Varying the Levels of Nitrogen in the Inflation Gas of Tires on Laboratory Test Performance

DISCLAIMER

This publication is distributed by the U.S. Department of Transportation, National Highway Traffic Safety Administration, in the interest of information exchange. The opinions, findings, and conclusions expressed in this publication are those of the authors and not necessarily those of the Department of Transportation or the National Highway Traffic Safety Administration. The United States Government assumes no liability for its contents or use thereof. If trade names, manufacturers' names, or specific products are mentioned, it is because they are considered essential to the object of the publication and should not be construed as an endorsement. The United States Government does not endorse products or manufacturers.

TECHNICAL REPORT DOCUMENTATION PAGE

1. Report No. DOT HS 811 094	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle The Effects of Varying the Levels of Nitrogen in the Inflation Gas of Tires on Laboratory Test Performance		5. Report Date November 2008	
		6. Performing Organization Code NHTSA/NVS-312	
7. Author(s) Larry Evans, John Harris - Transportation Research Center Inc. (TRC); Ed Terrill - Akron Rubber Development Laboratory, Inc.; James D. MacIsaac, Jr. - National Highway Traffic Safety Administration		8. Performing Organization Report No.	
9. Performing Organization Name and Address National Highway Traffic Safety Administration Vehicle Research and Test Center, P.O. Box B-37 East Liberty, OH 43319-0337		10. Work Unit No. (TRAIS)	
		11. Contract or Grant No.	
12. Sponsoring Agency Name and Address National Highway Traffic Safety Administration 1200 New Jersey Avenue SE. Washington, DC 20590		13. Type of Report and Period Covered Final	
		14. Sponsoring Agency Code	
15. Supplementary Notes			
<p>16. Abstract</p> <p>Air is approximately 78 percent nitrogen (N₂), 21 percent oxygen (O₂), and 1 percent other gases. The inflation of tires with gas mixtures containing more than 90 percent nitrogen has long been claimed to be beneficial to tire performance, and commercial systems that use nitrogen to inflate tires are widely available. In an effort to study the effects of inflation gas composition on vehicle tire performance, new passenger car tires and light-truck tires were inflated with nitrogen, air, or a 50/50 N₂/O₂ mixture and tested for performance in one of three laboratory tests: Static inflation pressure loss, rolling resistance, or accelerated oven-aging followed by a roadwheel durability test.</p> <p>In the 90-day static laboratory test, the inflation pressure loss for new tires inflated with nitrogen was approximately two-thirds of the loss rate of new tires inflated with air. Similar differences between nitrogen and air permeation rates in new tires were found under dynamic, loaded laboratory roadwheel testing. An analysis of oxygen levels in the inflation gas of 76 tires that were currently in service on passenger vehicles, and which were all originally inflated and topped-off with air (21% O₂), showed that the inflation gas dropped to an average of 15 percent O₂ after about three years of service. This can be attributed to the faster diffusion rate of oxygen through the tires relative to nitrogen during on-vehicle service, which increases the percentage of nitrogen in the tire cavity to well above the 78 percent N₂ in normal air. Therefore, barring tire punctures, deflation, etc., the relative benefits of nitrogen versus air inflation on pressure loss rate will reduce over time. The laboratory rolling resistance of new tires was tested at two different laboratories, using air or nitrogen inflation, and capped or regulated pressure. Inflating tires with nitrogen in place of air had no direct effect on laboratory rolling resistance performance. To evaluate long-term durability, new tires were broken in, inflated with air, nitrogen, or the standard (50/50 N₂/O₂) inflation gas, subjected to accelerated oven aging for five weeks at 65°C, then subjected to a 35.5-hour roadwheel durability test. All tires inflated with nitrogen (1 to 5% O₂) or air (21% O₂) passed the oven aging and roadwheel durability test sequence without failure. When the same tire models were oven aged with the standard 50/50 N₂/O₂ inflation gas, some exhibited premature failures on the roadwheel test, suggesting that oxidation had a deleterious effect on roadwheel durability.</p> <p>The primary result expected from nitrogen inflation is to enhance retention of tire pressure over time. Though inflation with nitrogen is not a substitute for regular pressure maintenance, the closer a tire operates near its recommended pressure, the less the penalties of underinflation such as rolling resistance loss, premature wear, and possible damage to the tire from over-deflection (overheating). Additionally, there is a strong scientific basis for concluding that reducing the oxygen content of the inflation gas will reduce the internal thermo-oxidative degradation of the tire, which may aid in retention of long-term durability.</p>			
17. Key Words Nitrogen, oxygen, tire, inflation pressure, permeability, rolling resistance, oven aging, FMVSS No. 139		18. Distribution Statement This report is free of charge from the NHTSA Web site at www.nhtsa.dot.gov	
19. Security Classif. (of this report) Unclassified	20. Security Classif. (of this page) Unclassified	21. No. of Pages 50	22. Price

ii:

Approximate Conversions to Metric Measures					Approximate Conversions to English Measures				
Symbol	When You Know	Multiply by	To Find	Symbol	Symbol	When You Know	Multiply by	To Find	Symbol
<u>LENGTH</u>					<u>LENGTH</u>				
in	inches	2.54	centimeters	cm	mm	millimeters	0.04	inches	in
ft	feet	30	centimeters	cm	cm	centimeters	0.4	inches	in
mi	miles	1.6	kilometers	km	m	meters	3.3	feet	ft
					km	kilometers	0.6	miles	mi
<u>AREA</u>					<u>AREA</u>				
in ²	square inches	6.5	square centimeters	cm ²					
ft ²	square feet	0.09	square meters	m ²	cm ²	square centimeters	0.16	square inches	in ²
mi ²	square miles	2.6	square kilometers	km ²	km ²	square kilometers	0.4	square miles	mi ²
<u>MASS (weight)</u>					<u>MASS (weight)</u>				
	ounces	28	grams	g	g	grams	0.035	ounces	oz
oz	pounds	0.45	kilograms	kg	kg	kilograms	2.2	pounds	lb
<u>PRESSURE</u>					<u>PRESSURE</u>				
psi	pounds per inch ²	0.07	bar	bar	bar	bar	14.50	pounds per inch ²	psi
psi	pounds per inch ²	6.89	kilopascals	kPa	kPa	kilopascals	0.145	pounds per inch ²	psi
<u>VELOCITY</u>					<u>VELOCITY</u>				
mph	miles per hour	1.61	kilometers per hour	km/h	km/h	kilometers per hour	0.62	miles per hour	mph
<u>ACCELERATION</u>					<u>ACCELERATION</u>				
ft/s ²	feet per second ²	0.30	meters per second ²	m/s ²	m/s ²	meters per second ²	3.28	feet per second ²	ft/s ²
<u>TEMPERATURE (exact)</u>					<u>TEMPERATURE (exact)</u>				
°F	Fahrenheit	5/9 (Celsius) - 32°C	Celsius	°C	°C	Celsius	9/5 (Celsius) + 32°F	Fahrenheit	°F

Table of Contents

SUBJECT:.....	1
PURPOSE:.....	1
EXECUTIVE SUMMARY:	1
BACKGROUND:	3
DEFINITIONS:.....	3
EXPERIMENTAL:.....	4
RESULTS:	5
SUMMARY:.....	32
REFERENCES:	34
ACKNOWLEDGEMENTS:.....	35
General Test Parameters	39
General Oven-Aging Test Procedures	40

List of Figures

Figure 1. Distribution of IPL Normalized to Air Rate = 100 for Tire Type. Normalized Distribution of Air and Nitrogen.....	8
Figure 2. Inflation Pressure Loss Versus Weeks on Test for Different Inflation Gas	10
Figure 3. Percent O ₂ Change During 90-Day Test Versus Initial O ₂ Concentration.....	11
Figure 4. Theoretical Distribution of IPL Normalized to Air Rate = 100 for Tire Type. Normalized Distribution of Air with 20.9% O ₂ , Air Depleted of O ₂ in Service, and Nitrogen	13
Figure 5. FMVSS No. 139 Endurance and Low-Pressure Tests - New Tires	19
Figure 6. Tires Broken in and Oven Aged With Various Inflation Gases Versus Performance in FMVSS No. 139 Endurance and Low-Pressure Test Sequence	20
Figure 7. Partial Pressure of Oxygen in 50/50 Inflation Gas Versus Weeks in Oven for Capped Oven Aging at 60° C and 70° C.....	21
Figure 8. Partial Pressure of Oxygen for Each Week of 65° C Oven Aging, Weekly Vent and Refill of Tires.....	22
Figure 9. Changes in the Inflation Pressure During Capped-Inflation Roadwheel Testing	24
Figure 10. Changes in the Percent Oxygen of Inflation Gas During.....	25
Figure 11. Changes in the Partial Pressure of Oxygen During Capped-Inflation Roadwheel Testing.....	26
Figure 12. Changes in the Partial Pressure of Non-Oxygen Gas During.....	27
Figure 13. Changes in the Level of Fixed Oxygen in the Skim and Wedge Rubber.....	28
Figure 14. Changes in the Average Tensile Properties in the Wedge Rubber Region,	29
Figure 15. Changes in the Average Tensile Properties in the Wedge Rubber Region,	30
Figure 16. Changes in the Inter-Belt Peel Strength in the Skim and Wedge Rubber	31

List of Tables

Table 1. SAS GLM Analysis of Inflation Pressure Loss	6
Table 2. Direct Comparisons of IPL for Nitrogen and Air Inflation	7
Table 3. Inflation Pressure Loss Rates for 50/50 N ₂ /O ₂ Versus Air and Nitrogen.....	9
Table 4. Inflation Pressure and Oxygen Percentage for Field Study Tires.....	12
Table 5. Estimated Composition of Tire Innerliner	14
Table 6. SAS GLM Analysis for Effects of Compound Composition Diffusion Rate (IPL)	15
Table 7. SAE J 1269 Single-Point Rolling Resistance Testing	16
Table 8. Direct Comparisons of Mean Values.....	17
Table 9. Analysis of Variance for Rolling Resistance (Three Tires of Each Type, Inflated With Air, Run Using Regulated Method, in Each Lab).....	17
Table 10. Predicted Rolling Resistance for N ₂ and Air-Inflated Tires After 90 Days Testing.....	18
Table 11. Figure 8 Linear Equations.....	22
Table 12. Modified LTDE Test Results.....	23
Table 13. LTDE Test Parameters.....	38
Table 14. Oven-Aging Test Parameters.....	39

Subject:

Differences in the laboratory test performance of tires when inflated with gas containing different ratios of nitrogen to oxygen.

Purpose:

The purpose of this report is to briefly detail results of NHTSA research that addresses the following basic questions that may affect the laboratory test performance of a tire when inflated with gases containing different ratios of nitrogen to oxygen:

1. Is there a systematic and quantifiable difference in the inflation pressure loss (IPL) of tires when inflated with gases of varying nitrogen-to-oxygen ratios?
2. Are any observed differences in IPL uniform among tires, or are they related to variables such as inflation pressure, or tire design and composition?
3. Are there direct effects of inflation gas composition on the rolling resistance of tires, or only indirect changes due to differing retention of inflation pressure over time?
4. Are there differences in tire durability performance after aging related to the nitrogen-to-oxygen ratio?

Executive Summary:

Air is approximately 78 percent nitrogen (N₂), 21 percent oxygen (O₂), and 1 percent other gases. The inflation of tires with gas mixtures containing more than 90 percent nitrogen has long been claimed to be beneficial to tire performance, and commercial systems that use nitrogen to inflate tires are widely available. NHTSA is currently conducting several tire research projects on the topics of tire inflation pressure loss rate, tire rolling resistance, and tire aging. In order to study the effects of inflation gas composition on aspects of tire performance, extra tires from the studies (generally tires that had been designated as back-up tires in the event of a mis-test) were inflated with nitrogen, and tested against tires inflated with air or other gases for performance in inflation pressure loss, rolling resistance, or oven aging followed by a roadwheel durability test.

In the 90-day static laboratory test, the inflation pressure loss for new tires inflated with nitrogen was approximately two-thirds of the loss rate of new tires inflated with air. The average 90-day pressure loss rate for tires inflated with air was 2.13 percent/month, and for the average for tires inflated with gas containing 95 percent to 99 percent nitrogen was 1.39 percent/month. Testing on a roadwheel indicated similar differences between nitrogen and air permeation rates under dynamic, loaded test conditions. A study of in-service tires on vehicles, originally inflated with air (21% O₂), showed O₂ levels averaging 15 percent for tires after about three years of service, which reduces the inflation pressure loss rate benefits for nitrogen inflation in service on a vehicle by approximately one-third. The decrease in permeability for nitrogen gas was observed to be independent of tire inner liner composition and thickness, thus applicable to all tire types studied.

As an example, one set of light-truck tires were inflated to 411.3 kPa (59.6 psi) with air that contained 21 percent O₂ and 78 percent N₂. At the end of 90 days the remaining pressure in the tire was 388.6 kPa (56.3 psi), an average inflation pressure loss rate of 1.72 percent/month (1.03 psi/month). When the light-truck tires were inflated with 99 percent N₂ gas, the pressure at the end of 90 days was 398.6 kPa (57.8 psi), an average inflation pressure loss rate of 1.24 per-

cent/month (0.74 psi/month). Over the 90 day period the percent N₂ in the air-inflated tire increased to 80 percent, and the percent N₂ in the nitrogen-inflated tire decreased to 98 percent, due to the faster permeation of oxygen gas through the tire components in both directions, in and out, depending on the balance of partial pressures. If we continue to replenish the inflation gas with the original gas mixture (air or 99% pure N₂) over a period of three years; the approximate predicted inflation pressure loss rates for the air-inflated tires, now containing 85 percent N₂, would be 1.57 percent/month (0.94 psi/month), relative to a predicted inflation pressure loss rate for the nitrogen-inflated tires of approximately 1.31 percent/month (0.78 psi/month), and now containing 95 percent N₂.

Thus, for the light-truck tire example provided above, the use of nitrogen-inflated tires decreased the amount of pressure lost by 28 percent over the first 90 days, while the predicted advantage of using nitrogen decreased to 17 percent over a three-year period compared to an air-inflated tire. If we take the average of all tires we tested, the use of nitrogen-inflated tires decreased the amount of pressure lost by 35 percent over the first 90 days, while the advantage of using nitrogen is predicted to decrease to 24 percent over a three-year period compared to an air-inflated tire.

The study indicated that inflating with nitrogen in place of air had no immediate effect on laboratory tire rolling resistance. However, it is estimated that at the end of 90 days of on-vehicle service with no inflation pressure maintenance, the improved retention of inflation pressure using nitrogen versus air inflation will result in a 1.5-percent reduction in tire rolling resistance.

Tires tested on a roadwheel after accelerated oven aging with nitrogen inflation showed no improvements in tire durability when compared to tires oven aged with air inflation. However, the oven aging test conditions may have been too short to differentiate between nitrogen and air inflation. Tires of same models oven aged with the traditional oxygen-rich inflation gas (50/50 N₂/O₂) exhibited multiple failures, indicating the higher oxygen levels had a deleterious affect on post-oven roadwheel durability. These laboratory results are supported by results from tires retrieved from on-vehicle service in Phoenix, Arizona, that indicate that a portion of the oxygen permeating through the tire reacts with the internal tire rubber compounds, leading to degradation of their material properties. Thus lowering the percentage of oxygen in the inflation gas may be one way to lessen the availability of oxygen to react with and degrade the internal components of the tire over a long period of service.

It should be noted that inflation with nitrogen merely slows the rate of diffusion of gas from the tire and is not a substitute for regularly maintaining tire pressure. The primary result expected from nitrogen inflation is to enhance retention of tire pressure over time, which will help maintain tire performance properties such as rolling resistance, handling, and durability. Since nitrogen and oxygen can diffuse both in and out of the tire over time, and the tire material properties may evolve and influence permeation rates, the authors caution that the results of laboratory testing on brand new tires may not predict benefits over a long period of real world service.

Background:

Air is approximately 78 percent nitrogen (N₂), 21 percent oxygen (O₂) and 1 percent other gases and contains a widely varying amount of water vapor. The inflation of tires with gas mixtures containing more than 90 percent dry nitrogen has long been claimed to be beneficial to tire performance, and commercial systems that use nitrogen to inflate tires are widely available.¹⁻¹⁰ Lower rates of inflation pressure loss are explained by a combination of lower rate of diffusion of the N₂ molecule through the rubber compound³ and by the reduced partial pressure of O₂ molecules inside the tire cavity.⁴ *Consumer Report's* magazine recently reported a comparison of the static inflation pressure loss of tires inflated with nitrogen versus those inflated with air.¹¹ The magazine concluded that inflation with nitrogen did slow down the rate of pressure loss from tires that were stored for one year, but questioned whether the cost of approximately \$5/per tire for nitrogen inflation was justified by this data. ExxonMobil Chemical has reported that tires maintained better durability and showed less separation at the belt edge when nitrogen was used as the inflation gas rather than air.¹² Exxon's report concluded that this improvement was correlated to a lower rate of inflation pressure loss. The benefit of improved inflation pressure loss to improve tire rolling resistance has also been shown to be significant.¹³ NHTSA is currently conducting several tire research projects on the topics of tire aging, inflation pressure loss rate and tire rolling resistance. In order to study the effects of inflation gas composition on aspects of tire performance, extra tires from the studies (generally tires that had been designated as back-up tires in the event of a mis-test) were inflated with nitrogen, and tested versus tires inflated with air for performance in inflation pressure loss, rolling resistance, or oven aging followed by a roadwheel durability test. This study was not a designed experiment to test inflation gases, but a small subset of testing added to current projects.

Various aging studies have shown that in order to simulate the results of aging in service, the oxygen content of the inflation gas needs to be increased beyond normal atmospheric levels of ~21 percent.¹⁴⁻¹⁶ Therefore, a small subset of tires were also inflated with 50 percent N₂/50 percent O₂ gas and included in the study to further differentiate the effects of the oxygen content of the inflation gas on performance. It should be stressed that because this data uses extra tires added onto existing research, comparisons of properties is limited, and much of the analysis will be descriptive in nature. Additional research could be conducted with a larger sample of tires to make direct comparisons with more precision.

Definitions:

<i>Air</i> (Also <i>Shop Air</i>)	Refers to normal atmospheric air compressed by mechanical means to inflate tires. Generally contains ~78% N ₂ /~21% O ₂ and varying levels of water vapor.
<i>Nitrogen</i>	N ₂ gas, either generated by separation from air onsite (approximately 95% - 99% N ₂), or received in pressurized cylinders (99+% N ₂), usually with very little or no humidity.
<i>Inflation Pressure Loss rate, (IPL)</i>	The rate of change of normalized inflation pressure, determined from the slope of the linear portion of the log pressure versus time curve as measured per ASTM F 1112.
<i>Rolling Resistance (RR)</i>	The force at the axle in the direction of travel required to make a loaded tire roll. Reported in pounds force. Corresponds to the energy lost by a tire

	to internal forces, and not transmitted to vehicle movement. For the free-rolling tire, it is the scalar sum of all contact forces tangent to the test surface and parallel to the wheel plane of the tire.
<i>Rolling Resistance Coefficient (RRC)</i>	The ratio of rolling resistance force to the load on the tire. Reported as a dimensionless unit, generally ranging from 0.007 to 0.014 for light vehicle tires.
<i>Light Vehicle</i>	NHTSA safety standards are applicable to vehicles with a gross vehicle weight rating of 4,356 kg or less (10,000 lbs. or less).
<i>Field Tires</i>	Tires tested during on-vehicle service or after having been retrieved from on-vehicle service.
<i>Tire Service Aging</i>	The changes in tire chemical and physical properties that take place as a tire is in service on a vehicle. Measured directly, or as a change in performance on a tire durability test.
<i>Tire Laboratory Aging Test</i>	A laboratory test designed to simulate the chemical and physical property changes, and tire durability test performance characteristics of a tire that has been in service on a vehicle.
<i>Base Inflation Pressure</i>	The inflation pressure corresponding to the maximum load listed in the tire load tables of the current T&RA yearbook or in corresponding tables published by similar organizations concerned with standardization.
<i>Capped</i>	When a tire is inflated to measure pressure loss, the capped method requires the tire pressure to not be adjusted during the test. This is done by inflating the tire to the required pressure prior to testing, while the tire is at ambient temperature of the test area, and then sealing the air in the tire during testing with a valve, cap or some other seal.
<i>Regulated</i>	During a test procedure, the inflation pressure is maintained at a specified value throughout the test.
<i>T&RA</i>	Tire and Rim Association, Inc. 175 Montrose West Ave., Suite 150 Copley, Ohio 44321

Experimental:

Tires were tested for inflation pressure loss using the ASTM F 1112 *Standard Test Method for Static Testing of Tubeless Pneumatic Tires for Rate of Loss of Inflation Pressure*. The ASTM F 1112 test method determines the rate of inflation pressure loss resulting from gas diffusion through the structures of tubeless tires under constant temperature conditions. The testing is done under static conditions, that is, non-rotating, non-loaded tires. Test tires are mounted on rims, fitted with calibrated precision pressure measuring devices, inflated to the desired pressure, and, after a period of stabilization, the inflation pressure is monitored as a function of time under static, constant temperature conditions. The test temperature was maintained at 21° C for all testing. Measured inflation pressures are then normalized to the nominal test temperature and one atmosphere barometric pressure (101.3 kPa) for calculation of pressure loss rates. The inflation pressure loss rate is calculated as percent loss per month using the slope of the linear portion of the log pressure versus time curve. The normal F 1112 test discards the first 30 days of data. During these tests the 90-day calculation follows this recommended practice. However to gener-

ate the 3-, 6-, 9-, and 11-week IPL values for this study, the first 30 days of data had to be included.

The rolling resistance of tires was measured using the SAE J 1269 Rolling Resistance Measurement Procedure for Passenger Car, Light Truck, and Highway Truck and Bus Tires for the laboratory measurement of rolling resistance of pneumatic tires. SAE J 1269 contains three different methods of determining rolling resistance: Force, Torque and Power. For this study the Force method was used in the two laboratories. The Force method measures the reaction force at the tire spindle and converts it to rolling resistance. These measurements are made using a 1.707 m roadwheel with an instrumented axle for the tire. The surface is covered with a medium-coarse (80 grit) texture. Test data is normalized to 24° C. The test conditions used were the Standard Reference Condition (SRC) using 70 percent of maximum T&RA load and base inflation pressure +20 kPa with a test speed of 80 km/h. During this part of the study both capped and regulated inflation methods were used. During the tests using the capped method the tire would be inflated at room temperature with the designated filling gas and then run with a 30-minute warm-up to stabilize the temperature and allow the pressure to build up as if it were on the highway. The regulated testing would be inflated using a rotary union to adjust the pressure and maintain the specified test pressure after the 30-minute warm-up, duplicating the standard SAE J 1269 test procedure.

The various projects involving nitrogen tire inflation involved the testing of 261 tires of 30 different models. Details of the different tire models are listed in Appendix A.

In addition to testing of inflation pressure loss, tires were tested in accordance with a dynamic aging protocol supplied by Michelin Tire in which the tire is run for an extended period of time on a laboratory roadwheel. Tires were also tested by laboratory aging in hot-air circulating ovens, followed by endurance testing on a laboratory roadwheel.

The modified Michelin Long Term Durability Endurance (LTDE) test procedure is shown in Appendix B.

Oven aging was carried out on tires mounted on rims and inflated with the specified gas at 65° C in a circulating-air oven. The procedure is shown in Appendix C.

Roadwheel testing of tires following oven aging was carried out using the FMVSS No. 139 endurance and low-pressure tests, as specified in the Code of Federal Regulations Part 571.139; New pneumatic radial tires for light vehicles, S6.3, Tire Endurance, and S6.4, Low Inflation Pressure Performance, shown in Appendix D.

All data used in the compilation of this report is available in an Excel spreadsheet that accompanies the report.

Results:

- 1. Is there a systematic and quantifiable difference in the inflation pressure loss of tires when inflated with gases of varying nitrogen to oxygen ratios?*

The initial analysis was done on the main body of tires that were inflated with air or with nitrogen. The few tires inflated with 50/50 N₂/O₂ will be analyzed separately. All inflation pressure loss data is in the accompanying Excel spreadsheet. Table 1 shows the SAS General Linear Model analysis at $\alpha = 0.05$ using the variables; tire type, whether individual tires were inflated with nitrogen or air, and whether tires were tested at Standards Testing Labs or Akron Rubber Development Lab. The overall model is significant with an R² of 0.902 with an F Value of 22.56. As expected, tire type is a significant variable with an F Value of 17.5 and a probability > F of 0.0001. The differences between test labs is not significant, while the inflation gas of N₂ versus air is significant with an F Value of 73.9 and a probability > F of 0.0001.

Table 1. SAS GLM Analysis of Inflation Pressure Loss

Dependent Variable: IPL Rate @ 90 Days, %/month						
Source	DF	Sum of Squares	Mean Square	F Value	Pr > F	
Model	27	56.41107497	2.08929907	22.56	<.0001	
Error	66	6.11121317	0.09259414			
Corrected Total	93	62.52228814				
	R-Square	Coeff Var	Root MSE	Rate_90d Mean		
	0.902255	17.62071	0.304293	1.726904		
Source	DF	Type III SS	Mean Square	F Value	Pr > F	
Inf_Gas	1	6.84238125	6.84238125	73.90	<.0001	
Test_Lab	1	0.01731799	0.01731799	0.19	0.6668	
Type	25	40.52978357	1.62119134	17.51	<.0001	

Table 2 shows a direct comparison between inflation with air or nitrogen, where these comparisons can be made using the same tire type. The third column shows whether the comparisons were significantly different at $\alpha = 0.05$ using the Duncan comparison of the SAS GLM procedure. In general, these comparisons are based on one tire inflated with nitrogen gas compared to one to three tires inflated with air. While only some of the comparisons are statistically significant, the average IPL for inflation with nitrogen is less than the IPL with air in every case. The last column shows the average IPL for nitrogen, divided by the average IPL for inflation with air for the same tire model. Figure 1 shows the distribution of IPL normalized to the mean rate for air loss for a tire type equal to 100. The average IPL with nitrogen is 65 percent of the average IPL for tires inflated with air. A GLM analysis by tire type and initial O₂ level in the tire produced a model with an overall R² of 0.896 with an F value of 95.22. Initial oxygen level is a significant variable with an F value of 59.44 and the estimate of its effect is that each 1 percent increase in O₂ produces an increase of 0.041 percent/month in IPL. There was no statistically significant correlation of IPL with either nominal or actual inflation pressure. This was not unexpected, particularly with this small sample set, since IPL is a percentage of the inflation pressure. There was also no significant correlation with the amount of oxygen lost during the test or the average ambient temperature within the small range recorded for the test. It should be noted that the IPL method corrects the reported data to a constant temperature and atmospheric pressure.

Table 2. Direct Comparisons of IPL for Nitrogen and Air Inflation

Tire Type	Individual Labs			
	Air, %/month	N ₂ , %/month	Significant Difference	Ratio, N ₂ IPL/Air IPL
B1	1.665	1.070	Yes	64.3%
B7	1.400	0.794	No	56.7%
B8	2.012	1.281	No	63.7%
B9	2.294	0.897	Yes	39.1%
C7	1.448	0.938	No	64.8%
C8	2.472	1.659	No	67.1%
D6	4.443	3.231	Yes	72.7%
G1	2.666	2.253	No	84.5%
M1	1.093	0.801	No	73.3%
M3	2.096	1.353	No	64.6%
N2	1.724	1.243	Yes	72.1%
O4	1.631	0.887	Yes	54.4%
P3	1.722	1.096	Yes	63.6%
S1	2.495	2.486	No	99.6%
T2	2.406	1.425	No	59.2%
U2	3.336	2.055	Yes	61.6%
Y2	1.256	0.679	No	54.1%
Average, Nitrogen as a Percent of Air				65.6%
Standard Deviation				13.2%

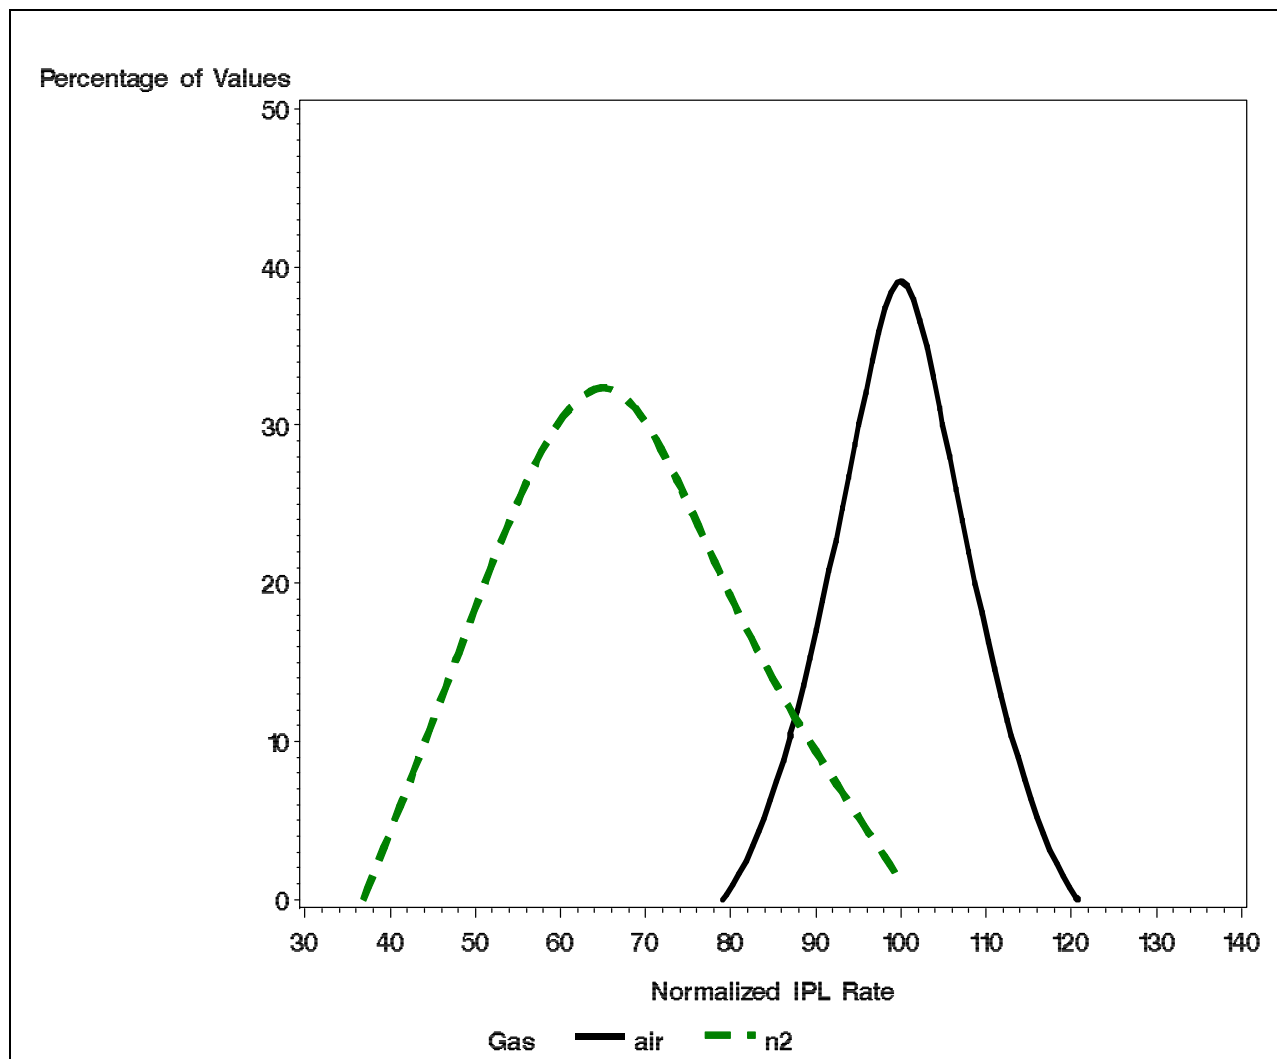


Figure 1. Distribution of IPL Normalized to Air Rate = 100 for Tire Type. Normalized Distribution of Air and Nitrogen

Inflating tires with nitrogen shows a significant advantage in reducing inflation pressure loss in the 90-day test conducted for these tires, therefore it is appropriate to address question two.

The addition of the few tires inflated with 50/50 N₂/O₂ to the analysis show conflicting results. The lower rate of IPL for the tires inflated with nitrogen has been shown to be a result of the lower diffusion rate of N₂ molecules through the rubber compound relative to O₂ molecules. The larger proportion of O₂ molecules in the inflation gas of the 50/50 mix should therefore lead to a dramatic increase in diffusion rate over air and a further increase over nitrogen. This was not observed in the 90-day IPL results as shown in Table 3.

Table 3. Inflation Pressure Loss Rates for 50/50 N₂/O₂ Versus Air and Nitrogen

Tire Type	Average IPL, %/month – 50/50 N₂/O₂	Average IPL, %/month – Air	Average IPL, %/month – N₂
B9	2.01	2.29	0.90
H3	1.93	-	0.81
M10	1.06	-	1.03
N1	1.62	-	0.80

Figure 2 shows the average IPL for tires inflated with air, nitrogen, and 50/50 N₂/O₂ mixture versus weeks on test, as well as the results for the individual tires that were inflated with the 50/50 mixture. In all cases the tires inflated with 50/50 N₂/O₂ showed significantly higher IPL at the three-week measurement and the rate decreased over time. Some of the tires inflated with nitrogen showed similar behavior, but at a much lower overall IPL. Research would be needed to ascertain whether this behavior is typical for all tires and what mechanism could be causing it to take place. Possible explanations are that the oxygen concentration builds up in the carcass of the tire during the initial period and therefore the tire cavity “sees” a partial pressure similar to that of the inflation gas which slows diffusion, or that oxidation causes changes in the physical and chemical properties of the tire components that affects the diffusion rate for the tire.¹

¹ As will be discussed, the initial and final oxygen concentrations and pressures of the gases during this experiment were measured, assuring that the unexpected results with 50/50 N₂/O₂ inflation were not artifacts of the test labs filling the tires with the incorrect inflation gases or pressure levels.

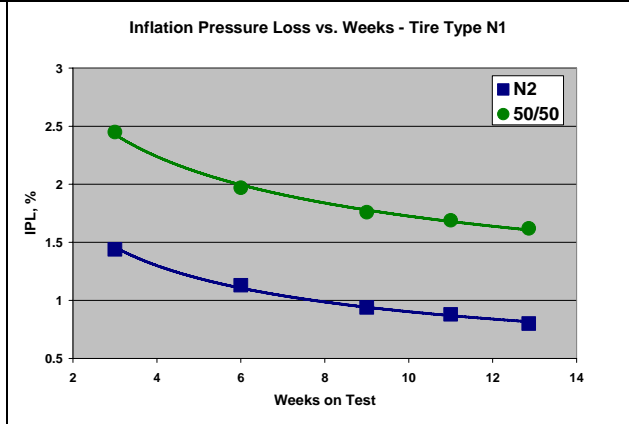
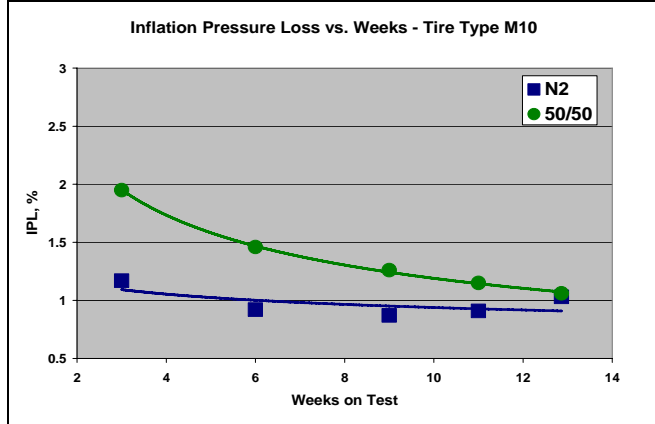
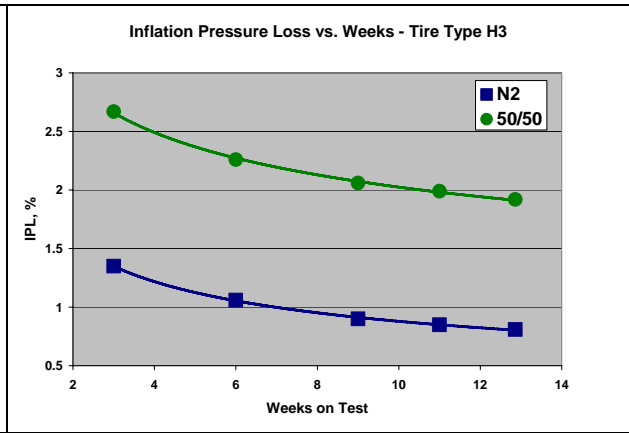
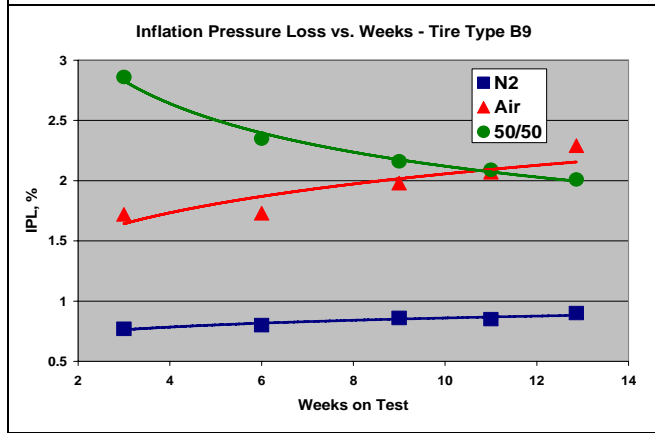
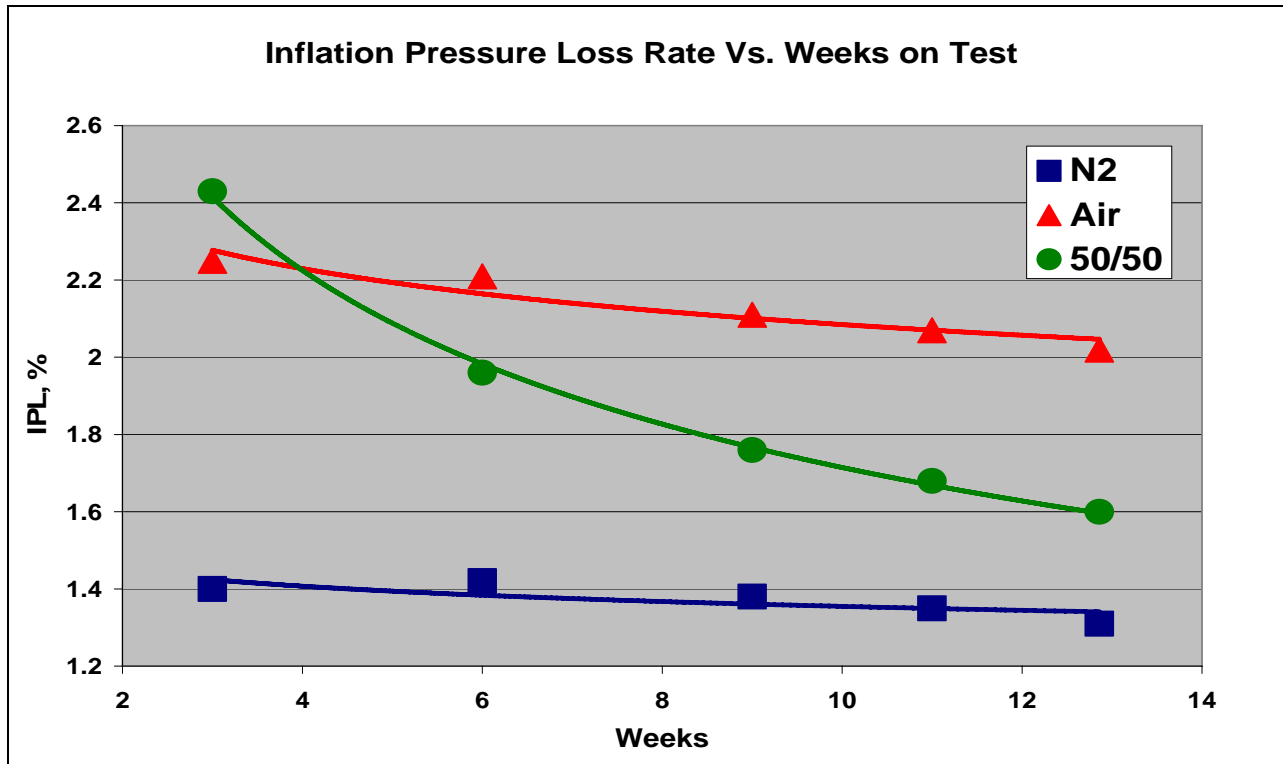


Figure 2. Inflation Pressure Loss Versus Weeks on Test for Different Inflation Gas

The concentration of oxygen was measured at the beginning and end of the 90-day test period for each tire. Figure 3 shows the change in oxygen concentration during the 90-day test versus the initial oxygen concentration. As expected, the tires with 50 percent initial oxygen concentration lost significantly more oxygen than nitrogen during the test. The data shows that tires inflated with air lost on average 1.5 percent oxygen concentration during the test. This finding supports the lower diffusion rate of nitrogen. Tires inflated with nitrogen of greater than about 97 percent purity actually gained oxygen during the 90-day test. This strongly indicates that the change in oxygen in the tire cavity is primarily a result of diffusion and not reactive consumption of the oxygen.

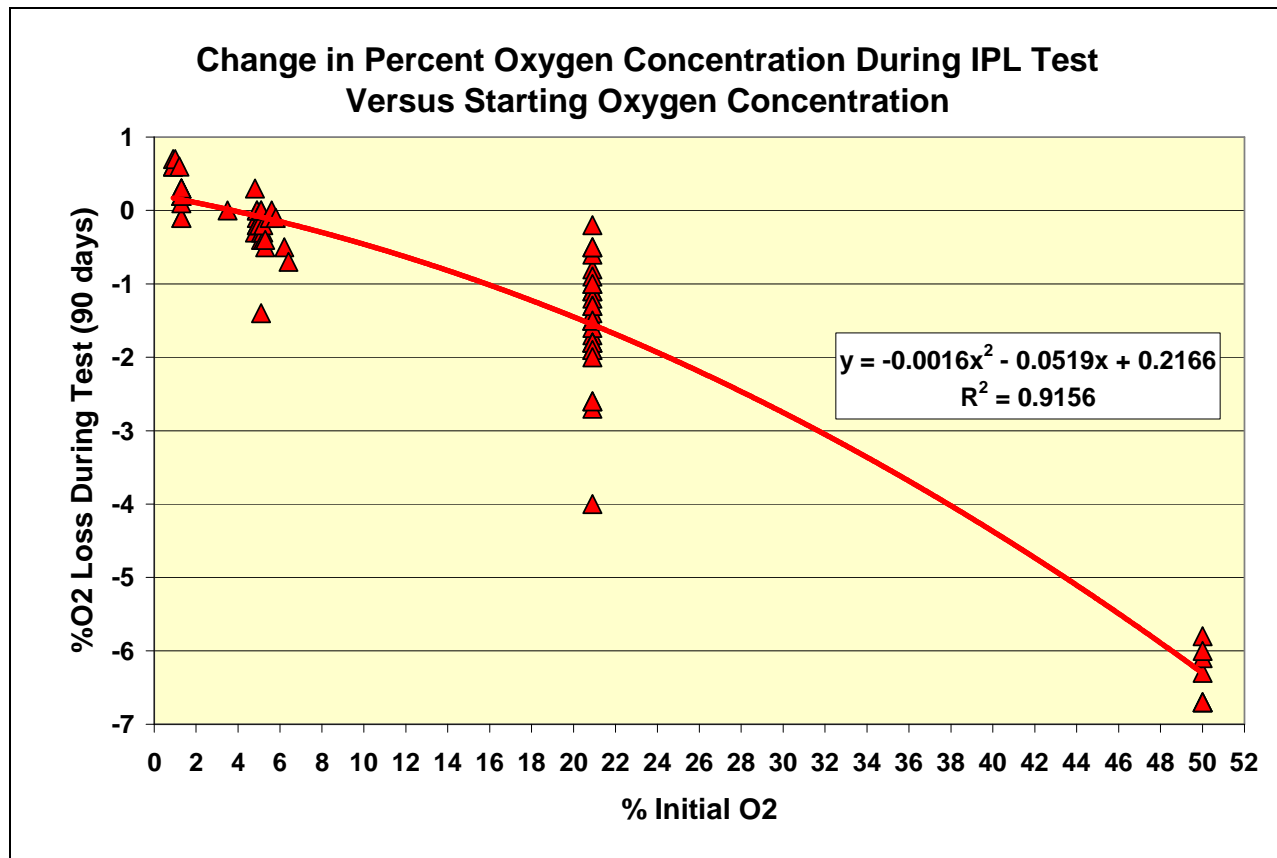


Figure 3. Percent O₂ Change During 90-Day Test Versus Initial O₂ Concentration

Seventy-six tires from 19 vehicles were measured for tire pressure and oxygen concentration. The tires were obtained on a volunteer basis from ARDL employees in Akron, Ohio. The tire pressures were measured with a pressure gauge (Pressure, Inc., Pro Series digital pressure gauge 0 to 160 psi in 0.5 psi units). The tire oxygen concentration was measured with an oxygen sensor (Parker IR637409-QE04299020 digital readout in percent with 0.1 units). The oxygen sensor was calibrated to 20.9 percent oxygen regularly between tire readings. For the 40 tires with the DOT date code recorded, the average age of the tires at the time of inspection was 2.8 years with tires ranging from 0.6 to 6.8 years old. The distribution of inflation pressure and oxygen percentage in the inflation gas is shown in Table 4. The average inflation pressure of the tires was 29.1 psi. Most tires (96%) were in a reasonable inflation range. However, three of the tires were severely underinflated (less than or equal to 15 psi). The average percentage of oxygen measured

in the inflation gas of field tires (on-vehicle tires) was 15.0 percent, and most values were significantly less than the original air inflation level of 20.9 percent. This suggests that the partial pressure of oxygen in the tire decreased significantly during service. Probably there are two contributing factors -- oxygen has a higher permeation rate than nitrogen, and second, oxygen is consumed by reaction with hydrocarbon compounds, especially the protective antidegradants.

Using the estimate of 0.041 percent/month for each percentage reduction in O₂ percentage and the average IPL loss of 2.13 percent/month for the tires studied in the lab, the calculated IPL of these field tires would be reduced by approximately 11 percent (0.24%/month) due to the change in inflation gas composition. In other words, if a normally maintained in-service tire is not punctured or dismounted, the faster diffusion/consumption of oxygen relative to the nitrogen content of the inflation gas results in an increase in the percentage of nitrogen gas from the original 78 percent to as high as the 91 percent observed, thus lowering the effective rate of inflation pressure loss. This means that the average loss rate for tires in the field may be considerably different than that measured using freshly inflated new tires. The calculated distribution for the field tires is shown in Figure 4. The broader distribution and lower mean IPL for the field tires means that the benefits of nitrogen inflation on pressure retention of tires in service may be overstated by testing with new, freshly inflated tires in a laboratory test. Based on this study, the mean advantage in IPL for tires in service will be approximately 25 percent for tires originally inflated with > 95% N₂ gas versus tires originally inflated with air.

Table 4. Inflation Pressure and Oxygen Percentage for Field Study Tires

Pressure Range (P.S.I)	Number of Tires	Oxygen Range (% of inflation gas)	Number of Tires
10.0 → 15	3	9 → 11	4
15.5 → 20	1	11.1 → 13	18
20.5 → 25	7	13.1 → 15	18
25.5 → 30	36	15.1 → 17	17
30.5 → 35	25	17.1 → 19	14
35.5 → 38.0	4	19.1 → 20.0	5
29.09	Average	15.02	Average
4.93	Standard Deviation	2.79	Standard Deviation

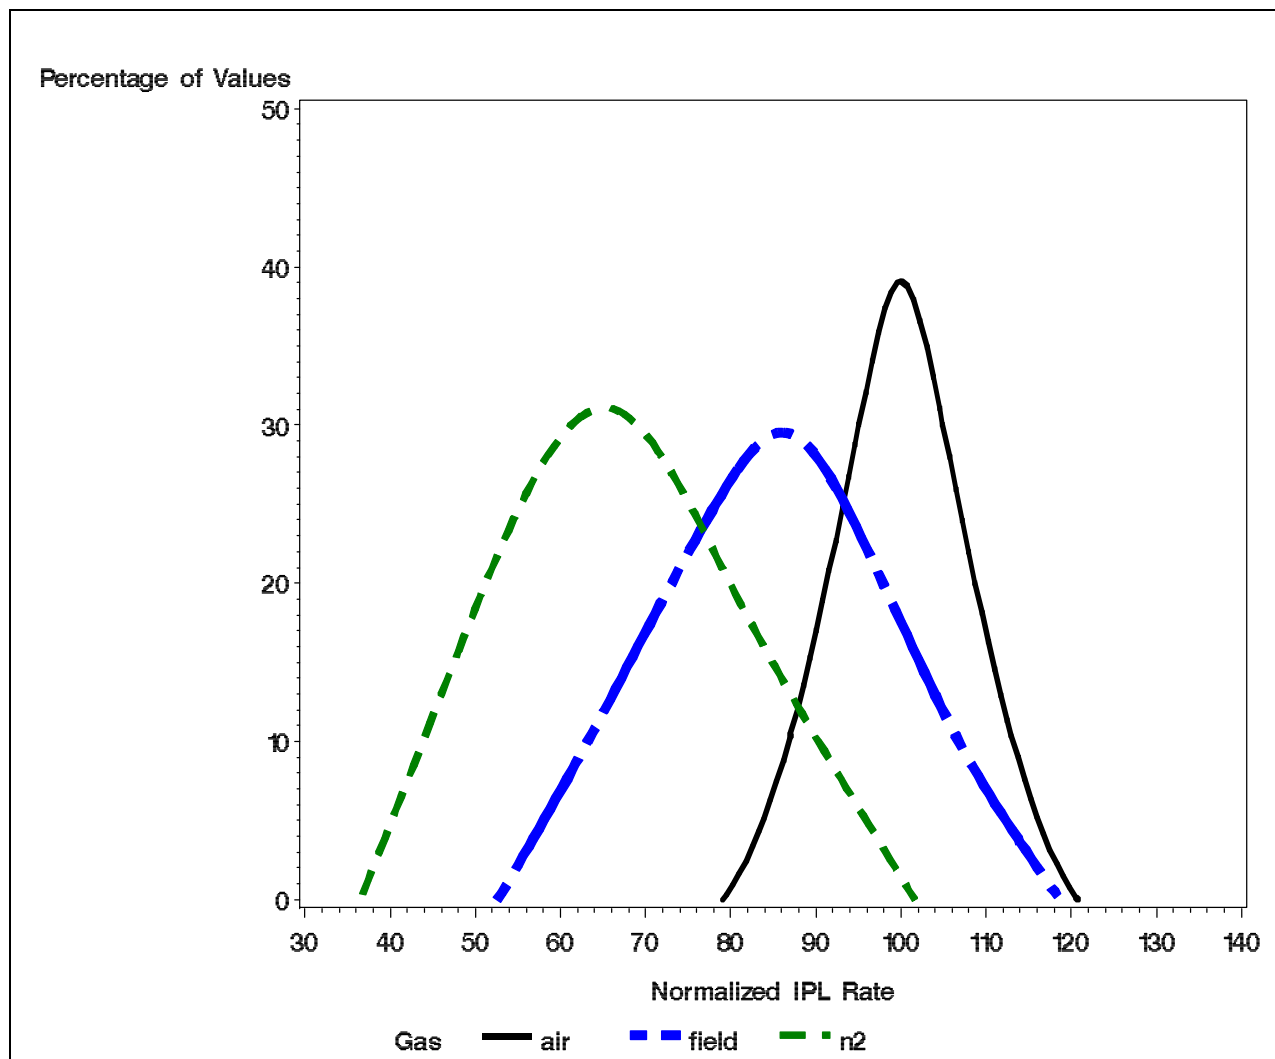


Figure 4. Theoretical Distribution of IPL Normalized to Air Rate = 100 for Tire Type. Normalized Distribution of Air with 20.9% O₂, Air Depleted of O₂ in Service, and Nitrogen

2. *Are any observed differences in IPL for nitrogen versus air uniform among tires, or are they related to variables such as inflation pressure, or tire design and composition?*

The composition of the inner liner was estimated by removing a section of the inner liner from the tire and testing it by pyrolysis-gas chromatography to identify the polymer composition and by thermal gravimetric analysis to separate the compound into volatile components (processing oil, curatives, moisture, etc.), polymer, carbon black, and non-black fillers (talc, clay, zinc oxide, etc.). All tires were analyzed and the data is included the accompanying Excel spreadsheet as Appendix E. Like-tires produced by the same manufacturer were combined to provide an average reconstruction of the rubber formulation for each tire inner liner shown in Table 5. Calculations representing the known values for two published formulations are shown for comparison and are generally in agreement with the values measured. It should be stated that reconstructing the composition of tire innerliners without prior knowledge of their ingredients is an imprecise process. Therefore, the values listed are estimates with a margin of error in the range of ± 5 phr (parts per hundred of rubber).

Table 5. Estimated Composition of Tire Innerliner

Tire Types	Halo- genated Isobutylene Rubber, phr	Natural Rubber, phr	Styrene- Butadiene Rubber, phr	Volatile Compo- nent, phr	Carbon Black, phr	White Filler, phr
B1, B7, B8, B9	85	15	-	16	76	5
C7, C8	65	30	5	14	74	5
D6	-	80	20	21	53	13
G1	90	10	-	18	72	11
H3	70	30	-	10	66	6
M1, M10	100	-	- ²	13	61	6
M3	90	10	-	11	61	6
N1, O4, P3	85	15	-	15	76	6
N2	50	40	10	12	59	28
S1	45	45	10	12	76	18
T2	55	45	-	12	71	22
U2	70	30	-	16	81	25
Y2	75	25	-	14	77	12
Vanderbilt Rub- ber Handbook, p. 609 (1990)	70	30	-	21	60	45
Rubber Technol- ogy, p. 108, Han- ser Press (2001)	100	0	-	15	50-60	3.5

The expected effects of compound variables on diffusion rate was seen for both nitrogen and air inflation. Increasing the level of halogenated isobutylene rubber (HIIR), the thickness of the liner,³ or the filler level significantly decreased the rate of diffusion. Increasing the level of volatile components (e.g., processing oil) increased the IPL. The results of the GLM analysis are shown in Table 6.

² Tires contained styrene resin which was not included as rubber phr

³ Innerliner samples were taken from the centerline region of the crown and measured. However innerliner thickness can vary considerably throughout in some tire designs. Additionally some tires do not have full bead-to-bead innerliners.

Table 6. SAS GLM Analysis for Effects of Compound Composition Diffusion Rate (IPL)

Model	R ²	F Value	Probability >F
	0.452	144.46	0.001
Variable	t Value	Probability > t	
HIIR	2.22	0.033	
Volatiles	1.89	0.067	
Black Filler	4.23	0.002	
White Filler	4.10	0.002	
Liner Thickness	3.33	0.002	

The difference between IPL when inflated with nitrogen versus with air (IPL_{Air} – IPL_{Nitrogen}) was analyzed by tire type using the SAS GLM procedure. This term was not significant with an R² value of 0.222 and an F value equal to 13.35, indicating that these variables do not have different overall effects for the two inflation gasses. No individual factor indicated a statistically significant effect on the difference in IPL for nitrogen versus air. The difference in IPL was also analyzed against both the nominal and actual starting inflation pressure. There was no significant effect found; model R² values were 0.034 and 0.027, respectively. In summary, the advantages in IPL for nitrogen inflation appear to be independent of tire type, inflation pressure, and innerliner thickness and composition.

3. Are there direct effects of the inflation gas composition on the rolling resistance of tires, or only indirect changes due to differing retention of inflation pressure over time?

Two light-truck tires; types D7 and D8, and two passenger tires, types G8 and G11, were tested for rolling resistance using the SAE J 1269 single-point method. Tires were measured by the Akron Rubber Development Laboratory, Inc., (ARDL) and by Smithers Scientific Services, Inc. (SMITHERS); inflated with air or N₂ gas; and run according to the standard method (*Regulated*), where the air pressure is regulated to the prescribed value throughout the test or the *Capped method*, where the pressure is allowed to increase as the tire heats to running temperature. The average test values for rolling resistance and the matrix used for comparisons are shown in Table 7. The comparisons that can be made for like conditions are shown in Table 8. The lab-to-lab (L/L) comparison was for the same tire types, using the same inflation gas, and the same method of inflation pressure maintenance during the test. Tires run at Smithers averaged 13.78 pounds while those run at ARDL averaged 13.51 pounds, a difference that can be attributed to the inherent variability of testing at different laboratories. Similarly, the regulated method produced a slightly higher force of 12.67 pounds, when directly compared to the 12.49 pounds for the capped method. This result is expected due to the rise in inflation pressure and resulting drop in rolling resistance as the capped tire heats up on the dynamic test, versus the regulated tire that vents the rising pressure to maintain the original pressure level. Finally, tires inflated with nitrogen gas produced a slightly lower rolling resistance of 12.65 pounds compared to 12.80 pounds for like tires inflated with air (a 1.2% difference). The SAS GLM analysis estimates that these differences are significant at $\alpha=0.10$ using the Duncan correction. Since most of the data is from single tires, this estimate must be viewed with extreme caution.

The SAS ANOVA (Analysis Of Variance) procedure for the tires inflated with air and tested using the regulated method is shown in Table 9. These tires were all run in triplicate and this is the best estimate of test-to-test variation that can be obtained from this data. The mean square error for this data is 0.11 pounds. This means that the difference of 0.15 pounds for air versus nitrogen inflation found in this study is within the expected range of variability and probably should not be accepted as statistically significant from this data. Therefore, testing and analysis of a larger population of tires may be needed. The relationship between increased inflation pressure and lower rolling resistance is well documented.^{1,10,13} Any major benefits to vehicle fuel economy from inflation of tires with nitrogen in place of air would therefore be expected as a result of the enhanced retention of inflation pressure over time, rather than any direct effect of nitrogen inflation gas.

Table 7. SAE J 1269 Single-Point Rolling Resistance Testing

Tire Type	Inflation Gas	Lab	Regulated/Capped	Mean Rolling Resistance, lbs	Number of Tires	Comparisons ⁴
D7	AIR	ARDL	Regulated	20.38	3	L/L N/A
D7	AIR	SMITHERS	Regulated	20.74	3	L/L
D7	N2	ARDL	Regulated	20.22	2	R/C N/A
D7	N2	ARDL	Capped	19.78	1	L/L R/C
D7	N2	SMITHERS	Capped	19.93	1	L/L
D8	AIR	ARDL	Regulated	20.10	3	L/L N/A
D8	AIR	SMITHERS	Regulated	20.59	3	L/L N/A
D8	N2	ARDL	Regulated	19.97	1	L/L R/C N/A
D8	N2	SMITHERS	Regulated	20.15	1	L/L R/C N/A
D8	N2	ARDL	Capped	19.94	1	L/L R/C
D8	N2	SMITHERS	Capped	20.21	1	L/L R/C
G8	AIR	ARDL	Regulated	8.24	3	L/L R/C N/A
G8	AIR	SMITHERS	Regulated	8.66	3	L/L N/A
G8	N2	ARDL	Regulated	8.18	1	L/L R/C N/A
G8	N2	SMITHERS	Regulated	8.31	1	L/L R/C N/A
G8	AIR	ARDL	Capped	7.81	2	R/C N/A
G8	N2	ARDL	Capped	8.05	1	L/L R/C N/A
G8	N2	SMITHERS	Capped	8.19	1	L/L R/C
G11	AIR	ARDL	Regulated	8.14	3	L/L N/A
G11	AIR	SMITHERS	Regulated	8.48	3	L/L N/A
G11	N2	ARDL	Regulated	7.92	1	L/L R/C N/A
G11	N2	SMITHERS	Regulated	8.36	1	L/L R/C N/A
G11	N2	ARDL	Capped	7.92	1	L/L R/C
G11	N2	SMITHERS	Capped	8.01	1	L/L R/C

⁴ L/L = Lab-to-lab comparison [ARDL versus Smithers]; R/C = Air pressure is regulated or capped during test procedure; N/A = Nitrogen to air filling gas comparison.

Table 8. Direct Comparisons of Mean Values

Comparison			Significant Difference
Lab-to-Lab (L/L)	ARDL	Smithers	Yes
	13.51	13.78	
Inflation During Test (R/C)	Regulated	Capped	Yes
	12.67	12.49	
Inflation Gas (N/A)	N2	Air	Yes
	12.65	12.80	

Table 9. Analysis of Variance for Rolling Resistance (Three Tires of Each Type, Inflated With Air, Run Using Regulated Method, in Each Lab)

The ANOVA Procedure					
Dependent Variable: RR					
Source	DF	Sum of Squares	Mean Square	F Value	Pr > F
Model	4	875.2690333	218.8172583	18179.0	<.0001
Error	19	0.2287000	0.0120368		
Corrected Total	23	875.4977333			
	R-Square	Coeff Var	Root MSE	RR Mean	
	0.999739	0.760924	0.109713	14.41833	
Source	DF	Anova SS	Mean Square	F Value	Pr > F
TYPE	3	874.3090333	291.4363444	24212.0	<.0001
Lab	1	0.9600000	0.9600000	79.76	<.0001

Twenty-five tire models have been tested for rolling resistance using the SAE J 1269 multi-point method, testing at different loads and inflation pressures. A regression analysis of the data showed a 0.85 percent increase in rolling resistance for each psi decrease in inflation pressure for passenger tires, and a 1.28 percent increase in rolling resistance for each psi decrease in inflation pressure for light-truck tires. This function is nearly linear over the range of rated inflation pressure +/- 10 psi. Based on these calculations the increase in rolling resistance for each tire model after three months of inflation pressure loss testing is shown in Table 10. The average increase in rolling resistance for tires inflated with air is 5.9 percent versus 3.9 percent for those tires inflated with nitrogen. Based on the predictions of the National Academy of Sciences¹³, a 2 percent advantage in rolling resistance would correlate to 0.2 to 0.4 miles per gallon increase in fuel economy. It should be noted that regular maintenance of inflation pressure is necessary for tires whether inflated with air or with nitrogen.

Table 10. Predicted Rolling Resistance for N₂ and Air-Inflated Tires After 90 Days Testing

TIRE TYPE	Rolling Resistance After 90 Days, % of Original	
	Air Inflation	N ₂ Inflation
B1	104.2	102.7
B7	103.6	102.0
B8	105.1	103.3
B9	108.8	103.4
C7	103.7	102.4
C8	106.3	104.2
D6	111.3	108.2
G1	106.8	105.7
M1	102.8	102.0
M3	105.3	103.5
N2	106.6	104.8
O4	106.3	103.4
P3	104.4	102.8
S1	106.4	106.3
T2	106.	103.6
U2	108.5	105.2
Y2	104.8	102.6
AVERAGE	105.9	103.9

4. Are there changes in tire durability performance after aging related to the nitrogen to oxygen ratio?

The accepted chemical mechanisms that produce material property changes in tires during service are thermo-oxidative.^{14,16,19} Numerous articles have been published that show benefits to slowing the rate of change in rubber properties by inflating tires with nitrogen in place of air.²⁻¹¹ Conversely, there have been several studies that use increased oxygen in the filling gas to accelerate these changes in properties to age the belt coat stocks of tires in a laboratory environment.¹⁴¹⁶⁻²⁰ Tires inflated with nitrogen were added to the NHTSA tire aging study in addition to the tires inflated with air or 50 percent N₂/50 percent O₂. Two new tires from each of 11 different tire models were subjected to the FMVSS No. 139 Endurance and Low Pressure roadwheel tests. All 22 new tires successfully completed the 35.5-hour test sequence with no visible findings (NVD), and no appreciable pressure loss. These results are detailed in Figure 5, which identifies tires as passenger or light truck, by manufacturer, by tire type (Appendix A), and by unique four-digit barcode.

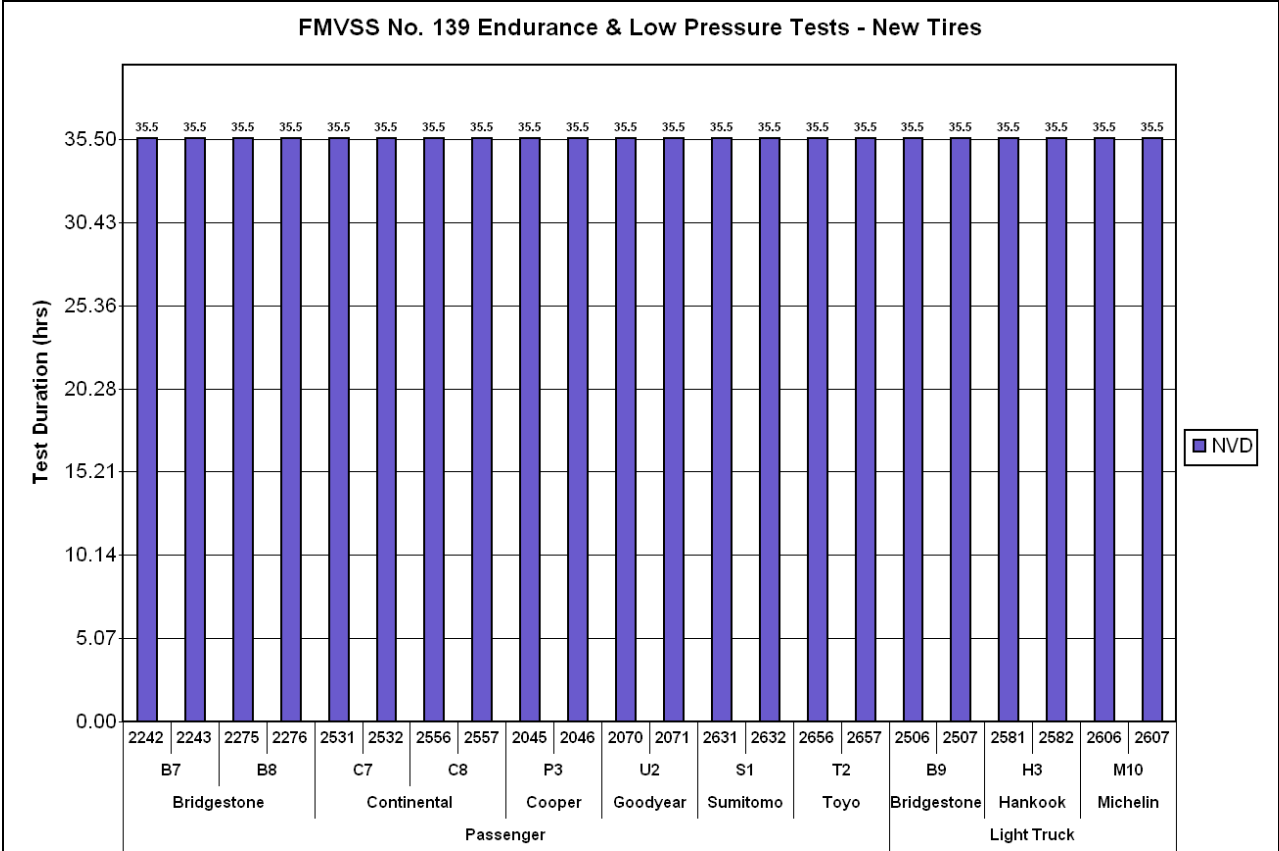


Figure 5. FMVSS No. 139 Endurance and Low-Pressure Tests - New Tires

Two new tires of each of 11 different tire models were subjected to a two-hour roadwheel break-in at 80km/h (50 mph), followed by a 5-week oven aging procedure (details in Appendix C) using a 50/50 N₂/O₂ inflation mixture, which yields an effective oxygen content of around 42 percent, or about twice the level of normal air. Based on an agency analysis of the changes in tire material properties and roadwheel performance in tires retrieved from service, these oven aging conditions replicate approximately 2.5 years and 47,000 kilometers (29,000 miles) of service in the high ambient temperatures of the Southwestern United States, or as much as double that amount of service in the northernmost States. One additional tire of each model was subjected to the same test procedure with shop air inflation (21% oxygen) and another tire with nitrogen inflation (3% oxygen) from a nitrogen generator unit. After aging tires inflated with the accelerated aging mixture of 50/50 N₂/O₂ inflation gas, 6 of 22 tires (27%) failed before the end of the 35.5-hour roadwheel test sequence due to thermo-oxidative degradation of the tire rubber compounds and their interlaminar interfaces. However, all 22 new tires with air or nitrogen inflation successfully completed the 35.5-hour test sequence with no visual findings (NVD) following oven aging. Therefore, no difference in performance in the post-aging roadwheel test was observed between oven aging with normal shop air and nitrogen for these test conditions.

FMVSS No. 139 Endurance & Low Pressure Tests - Following 2-hr Break-in @ 50 mph, 65 C Oven Aging for 5 Weeks, Weekly Vent and Refill of Inflation Gas

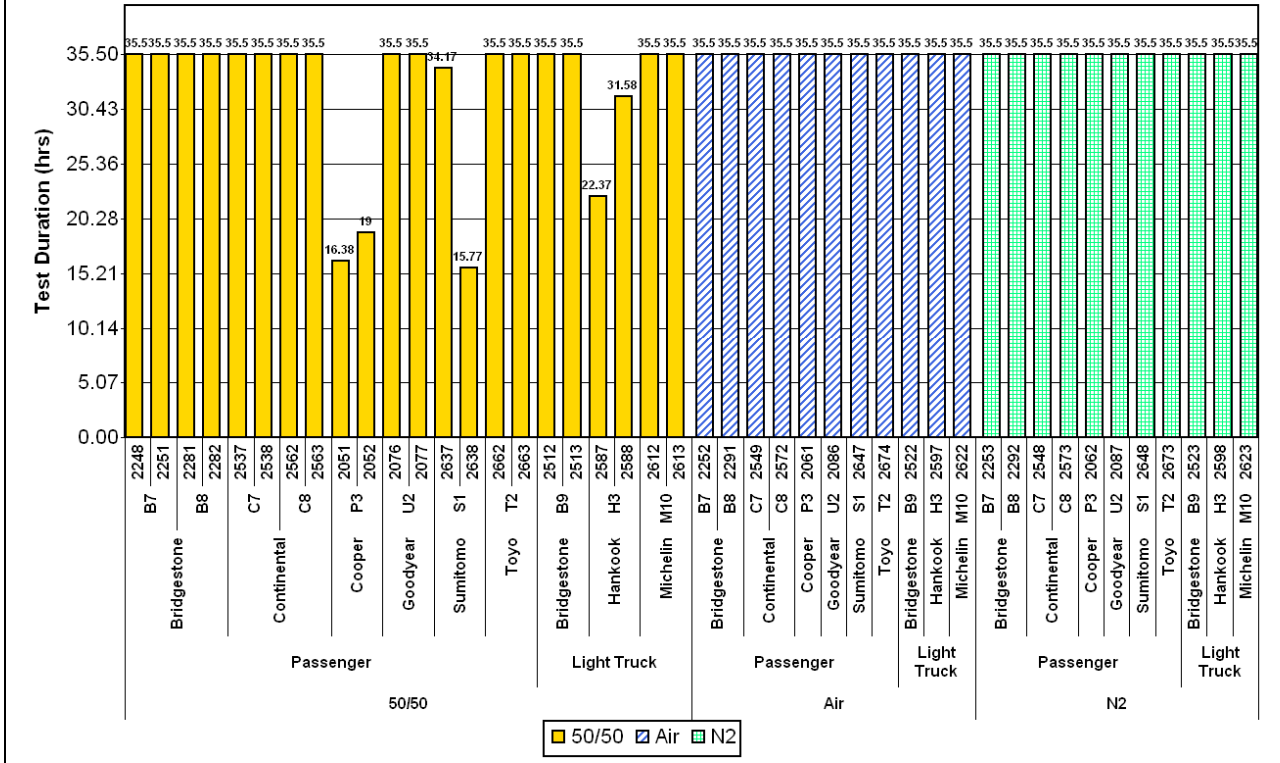


Figure 6. Tires Broken in and Oven Aged With Various Inflation Gases Versus Performance in FMVSS No. 139 Endurance and Low-Pressure Test Sequence

The oven aging comparison of the three gases yielded intuitive results. All new tires passed the performance requirement of 35.5 hours. If aging the tires with a 2-hour roadwheel break-in, followed by oven aging with 50/50 inflation for 5 weeks yields material properties equivalent to 2.5 to 5 years of service in the United States, then aging with half of that level of internal oxygen (air inflation) would likely produce minimal degradation in this short-duration test and no test failures. The results of aging with 50/50 N₂/O₂ inflation mixture and the underlying mechanisms behind thermo-oxidative degradation predict that difference between air and nitrogen inflation may have been observed if the test was more severe (i.e., longer oven aging period, longer roadwheel test, etc.)

At the end of each week of the oven aging documented in Figure 6, the tires were removed from the oven and allowed to cool to ambient laboratory temperatures. The inflation pressure was measured, the tire valve stem core was removed, inflation pressure vented, and the tire refilled to cold inflation pressure with fresh quantities of the appropriate gas. The goal of this “vent and refill” procedure during normal oven aging is to maintain a consistent level of oxygen partial pressure in the tire throughout the test, keeping the rate of oxidation from dropping precipitously during the procedure. For instance, Phase 1 of the Tire Aging Test Development Project collected 6 tire models from on-vehicle service in Phoenix, Arizona.²² Figure 7 displays the partial pressure of oxygen in new samples of these 6 tire models during 60° and 70° C oven aging with capped 50/50 inflation. The tires were filled to their maximum inflation pressure with 50/50, the valve

stem capped, and the tires oven-aged without interruption. One set of tires was removed after three weeks and the pressure and percentage of oxygen in the inflation gas was measured. Another set of tires repeated the procedure at six weeks. As is evident in Figure 7, the portion of the pressurized inflation gas that is oxygen (“partial pressure of oxygen”) is permeating and reacting so quickly that at six weeks, a normal passenger tire with a 35 psi max inflation pressure has lost one-third to half of the pressurized oxygen during the test, depending on the temperature. As oven aging test development progressed, it became evident that the pressure level and oxygen content level in the gas was going to have to be maintained in order to retain a sufficient oxygen for the oxidative reaction.

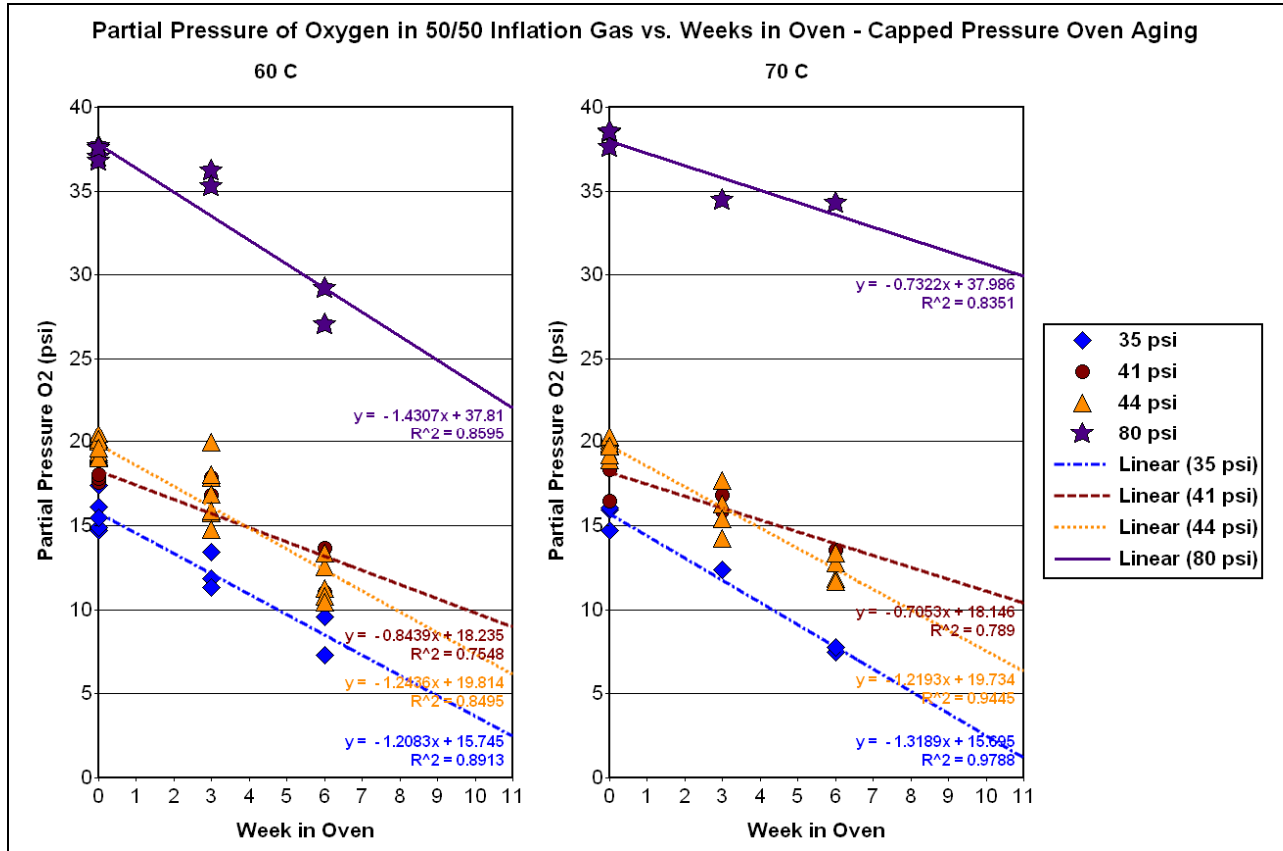


Figure 7. Partial Pressure of Oxygen in 50/50 Inflation Gas Versus Weeks in Oven for Capped Oven Aging at 60° C and 70° C

For tires inflated with 50/50 N₂/O₂ or N₂ in the Figure 6 inflation gas comparison, an extra step was taken to measure the percent oxygen in the inflation gas before venting the tire. With the weekly vent and refill of the 50/50 N₂/O₂ inflation gas, the partial pressure of oxygen remained essentially constant throughout the test. When nitrogen inflation was used, the partial pressure of oxygen initially dropped until nearly zero oxygen remained at week five. Since many lines are close together on the graph, equations for the linear regressions are contained in Table 11.

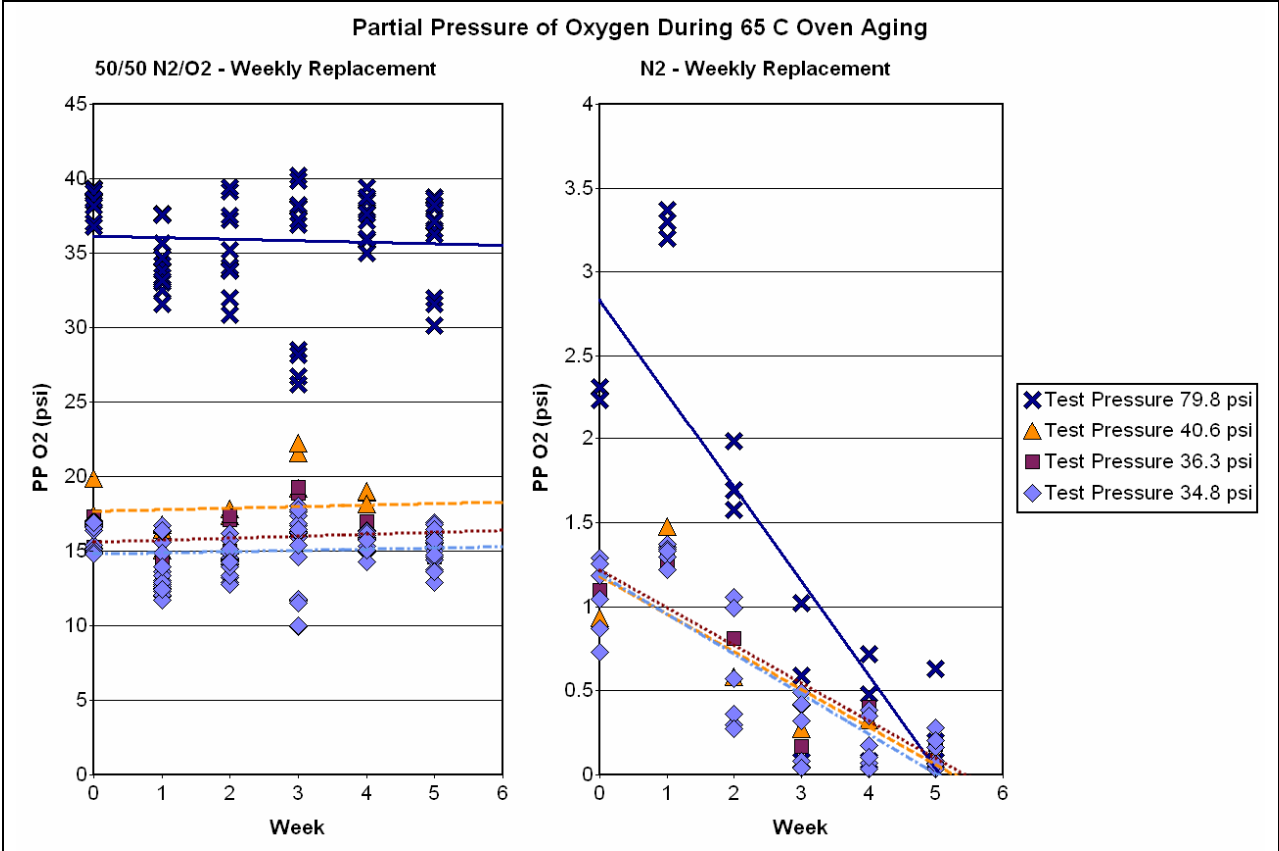


Figure 8. Partial Pressure of Oxygen for Each Week of 65° C Oven Aging, Weekly Vent and Refill of Tires

Table 11. Figure 8 Linear Equations

Test Pressure	50/50 N2/O2		N2	
	Equation	R ²	Equation	R ²
79.8 psi (550 kPa)	$y = -0.1033x + 36.157$	0.0029	$y = -0.5588x + 2.8301$	0.7211
40.6 psi (280 kPa)	$y = 0.1021x + 17.613$	0.0084	$y = -0.2240x + 1.1794$	0.6811
36.3 (250 kPa)	$y = 0.1313x + 15.549$	0.0175	$y = -0.2242x + 1.2175$	0.7788
34.8 (240 kPa)	$y = 0.0813x + 14.749$	0.0069	$y = -0.2376x + 1.1930$	0.7010

The observed changes in inflation pressure and percent oxygen content during the oven aging or IPL test are for tires in a static, unloaded state. To attempt to examine dynamic effects, new tires of the 6 models collected from service in Phoenix, Arizona, were subjected to a modified version of the Michelin LTDE roadwheel test protocol (Appendix B). Three different inflation gases were used in the experiment, resulting in initial oxygen concentrations of 45 percent (50/50 N₂/O₂), 21 percent (air), or 3 percent (nitrogen). The test was modified such that the initial tire pressure was set per specifications and not adjusted throughout the test rather than topped off every 24 hours as specified in the original procedure. At each 24-hour increment of the test the tire was stopped, ambient temperature was recorded, and the inflation pressure and oxygen content of the gas was measured. This resulted in a small loss of pressurized inflation gas with each measurement; therefore the dynamic pressure loss rates for this testing are moderately higher than for a purely capped test protocol. However, it is reasonable to assume that the pressure lost

during each measurement at the 24-hour mark was roughly the same regardless of the inflation gas, and therefore will be reasonably predictive of loss rates for the different gas mixtures experiencing similar dynamic, loaded tire conditions.

The durability results of the LTDE test are shown in Table 12. Once again, the small sample sizes and short duration of the test (relative to years of intended vehicle service) produced no useful trends in differentiating the effects of the various inflation gases on tire durability.

Table 12. Modified LTDE Test Results

Tire Type	Barcode	Inflation Gas	Time to Failure, Hours	Notes on Tire Failure Type
B	1014	50-50	.	Test interrupted @ 213 hours - Holiday shut-down
B	1009	50-50	622.5	Tread Shoulder Separation OSS, Belt Edge Exposed OSS, Bead Damage OSS.
B	1010	AIR	.	Test interrupted @ 213 hours - Holiday shut-down
B	1011	AIR	431.9	Tread Shoulder Chunking with Belts Exposed OSS, Belt Edge Separation OSS, Innerliner Split.
B	1012	N2	.	Test interrupted @ 213 hours - Holiday shut-down
B	1013	N2	349.5	Tread Shoulder Cracking OSS.
C	1511	50-50	.	Test interrupted @ 332 hours - Holiday shut-down
C	1510	50-50	536	Innerliner Separation, Sidewall Rupture SS, Total Air Loss.
C	1509	50-50	204.3	Sidewall Cracking SS and OSS.
C	1512	AIR	629.8	Sidewall Rupture SS, Total Air Loss.
C	1514	N2	526.5	Bead Turn-up Cracking SS, Bead Damage SS.
D	1109	50-50	354.9	Bead Turn-up Cracking OSS.
E	1350	50-50	494.2	Sidewall Cracking, Bead Damage SS.
E	1309	50-50	473.4	Bead Turn-up Cracking SS, Tread Shoulder Pocket Cracking SS and OSS.
E	1370	AIR	574.8	Tread Shoulder Chunking with Belts Exposed, Belt Edge Loosened, Bead Turn-up Cracking, Tread Shoulder Pocket Cracking
E	1313	N2	507.9	Tread Shoulder Chunking with Belts Exposed SS, Tread Shoulder Pocket Cracking SS and OSS, Bead Damage SS and OSS
H	1209	50-50	97.5	Sidewall Rupture with Delamination SS, Innerliner Separation, Total Air Loss.
H	1210	50-50	55.8	Sidewall Rupture with Delamination SS x 2.
H	1214	AIR	731.2	Sidewall Rupture with Delamination SS.
H	1212	AIR	515.2	Bead Turn-up Cracking OSS, Bead Damage OSS.
L	1409	50-50	667.8	Sidewall Cracking OSS, Innerliner Separation.
L	1411	AIR	717.5	Bead Turn-up Cracking SS, Total Air Loss.
L	1413	N2	647.1	Sidewall Cracking OSS.

Displayed in Figure 9 is the inflation pressure, corrected for temperature, for tire types “B,” “C,” “E,” or “L” that were subjected up to 700 hours of roadwheel testing with all three gases (in-

cludes pressure losses for pressure and percent oxygen readings taken every 24 hours). The initial cold pressure data point for each tire at 0 hours is not used, only the hot pressures from the 4-hour reading and onward. For comparison, it is estimated that the average tire in the United States experiences approximately 394 hours of use per year.⁵ The average time to removal for the 18 tires of the 4 tire models test was 464 hours, the equivalent of a little over one year of rolling service. Tires in the modified LTDE test results were observed to have slightly less pressure loss for nitrogen versus air inflation, and slightly less pressure loss for air versus 50/50 inflation. Based on the slopes of the linear regression lines, which have essentially the same y-intercepts, the nitrogen inflated tires lost inflation pressure at only 63 percent the rate of air inflated tires during the dynamic roadwheel testing. Additionally, the 50/50 inflated tires lost inflation pressure at 125 percent the rate of the air inflated tires. Therefore it is expected that the lower the percentage of oxygen in the tire inflation gas, the slower the rate of pressure loss during dynamic on-vehicle use.

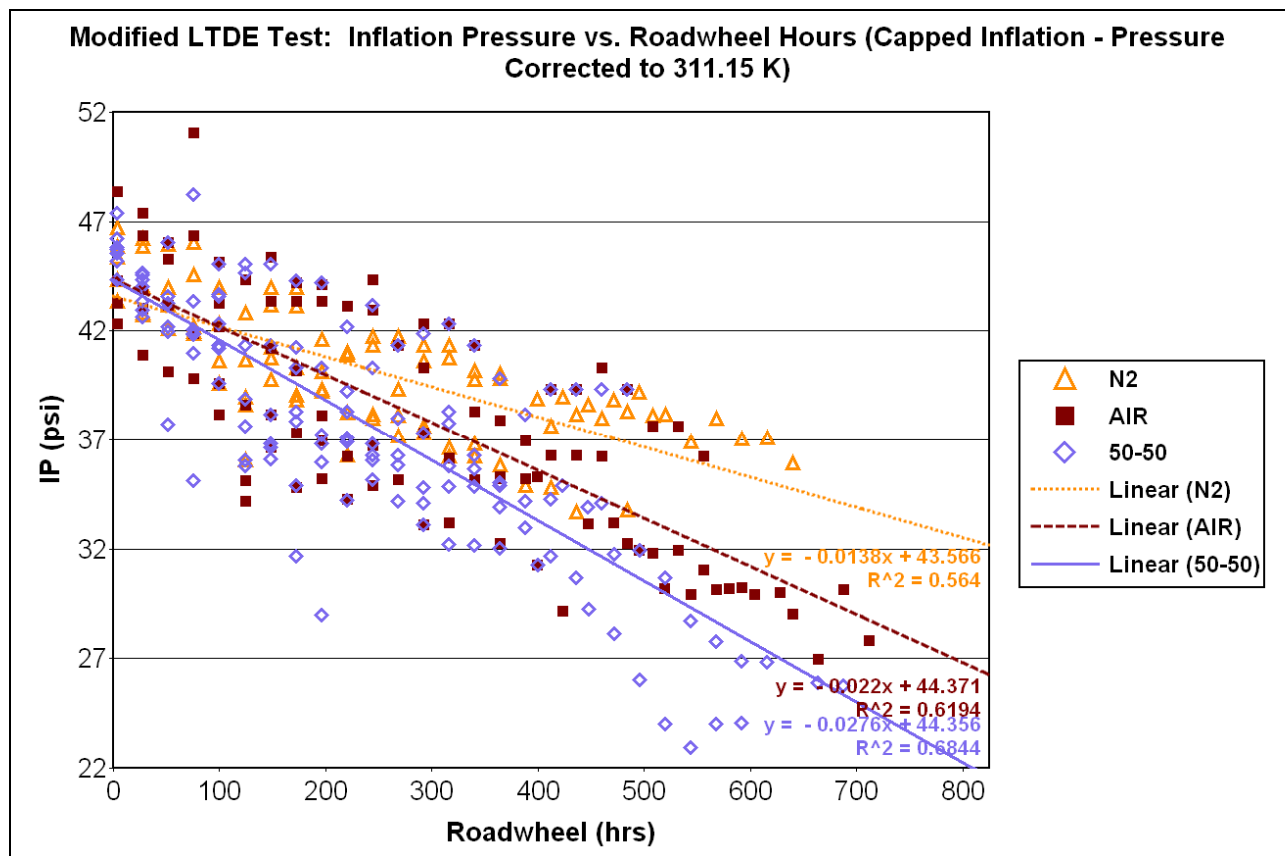


Figure 9. Changes in the Inflation Pressure During Capped-Inflation Roadwheel Testing

⁵ USDOT Bureau of Transportation Statistics, Highlights of the 2001 National Household Travel Survey: 29.1 miles per day per person/55.1 minutes per day of travel per person = average speed of 31.7 mph. 12,497 miles per year vehicle use/31.7 mph = 394 hours per year of vehicle use.

http://www.bts.gov/publications/highlights_of_the_2001_national_household_travel_survey/html/section_02.html, and Highway Statistics 2004, FHWA, Table VM-1, <http://www.fhwa.dot.gov/policy/ohim/hs04/htm/vm1.htm>

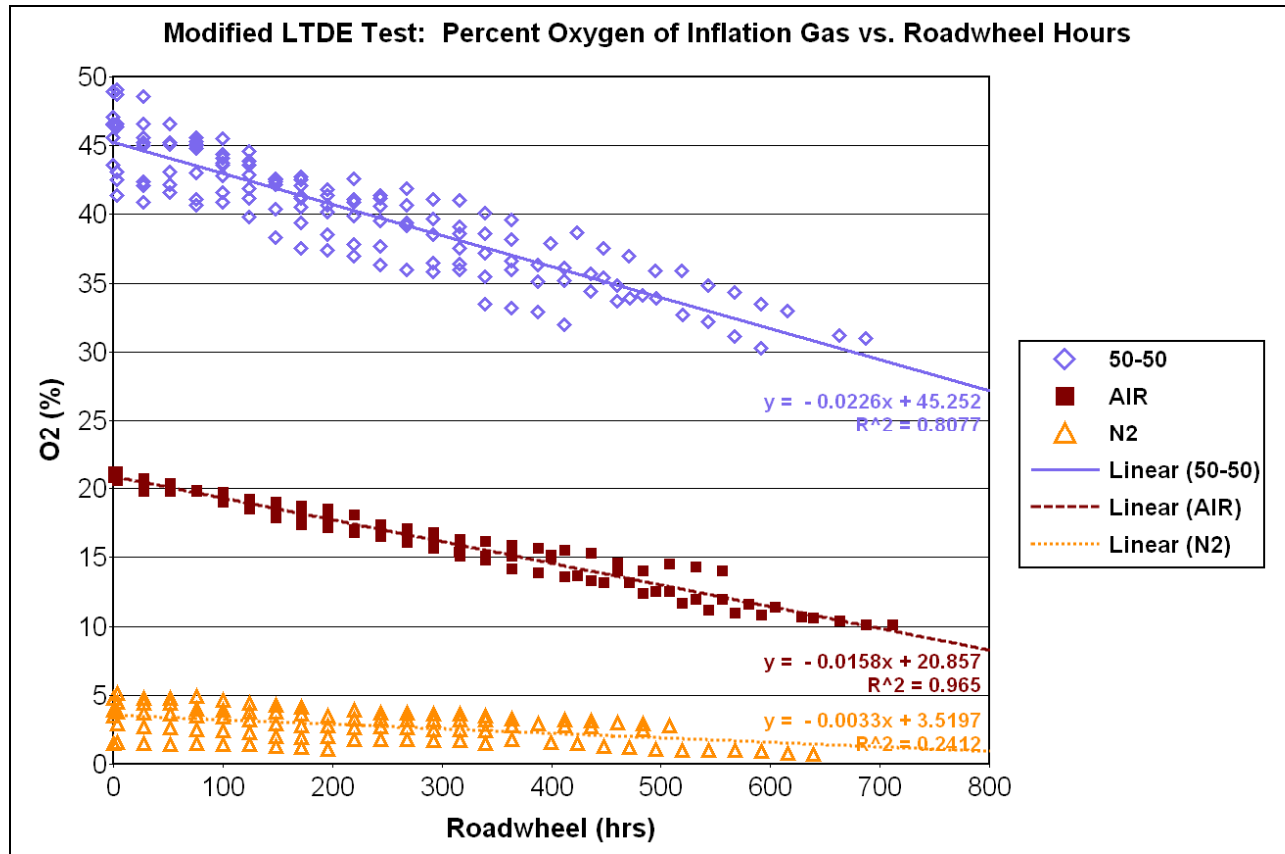


Figure 10. Changes in the Percent Oxygen of Inflation Gas During Capped-Inflation Roadwheel Testing

Figure 10 depicts the change in the percent of oxygen, as compared to the other components of the fill gases, during the course of the roadwheel test. If oxygen was diffusing out of the tire at the same rate as nitrogen, then the percentage of oxygen inside the tire would not change during the roadwheel test. In reality, the tires are diffusing or consuming oxygen during the test at a faster rate than other gases. In fact, tires inflated with 50/50 N₂/O₂ were down from 45 percent O₂ to 36 percent O₂ at the 394-hour point. Tires filled with normal air, which had half the initial percentage of O₂, were down from about 21 percent to 15 percent oxygen at the 394-hour mark. To better illustrate mechanisms at work, the pressure remaining in the tire at each measurement and the corresponding percentage of oxygen are multiplied to yield the “partial pressure” of oxygen in the tire. In Figure 11 the partial pressure of oxygen was plotted against time on the roadwheel. A rapid decline in the pressurized oxygen in the tire cavity is clearly visible for the 50/50 N₂/O₂, with less pressure loss for air inflation, and still less for nitrogen inflation.

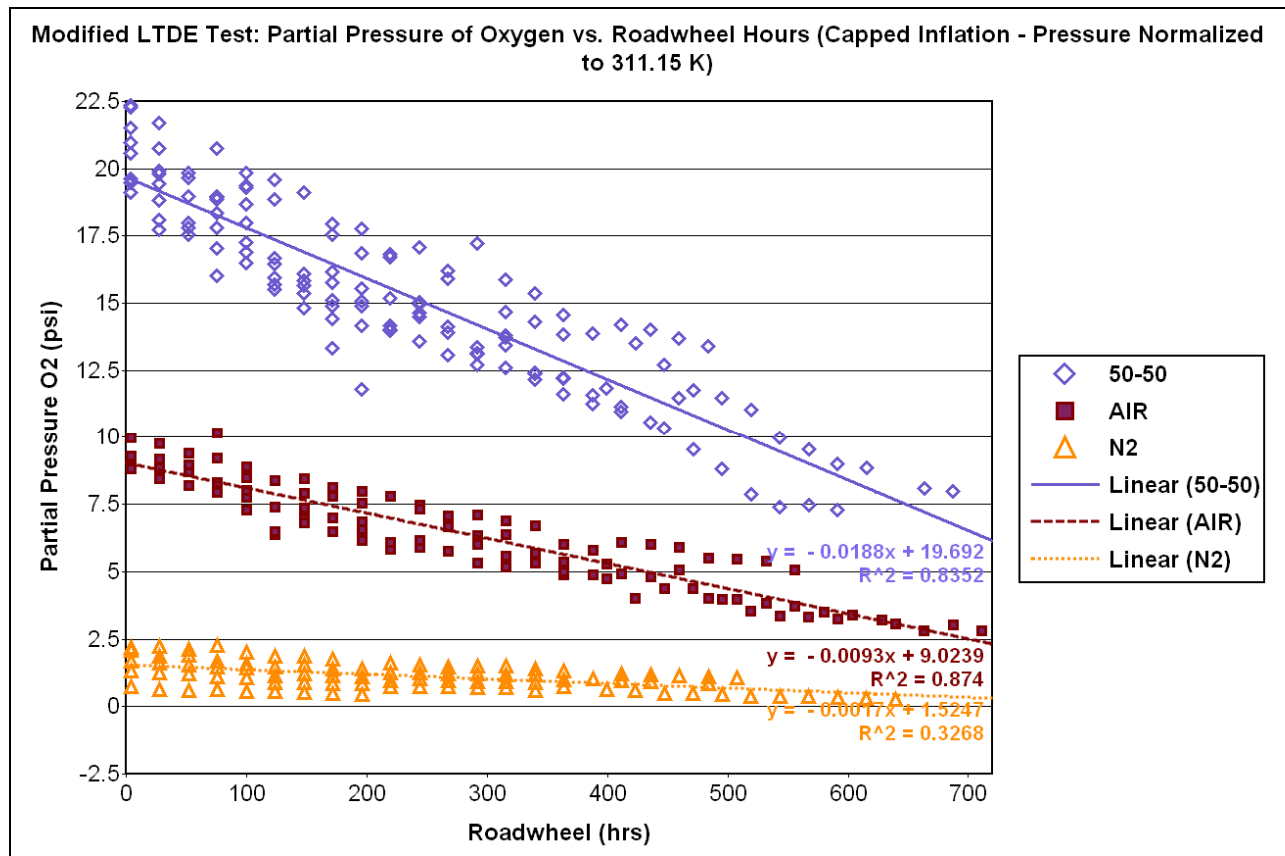


Figure 11. Changes in the Partial Pressure of Oxygen During Capped-Inflation Roadwheel Testing

In Figure 12 the pressure of the remaining gases (which are 99 percent nitrogen) is displayed. The slopes for the three overall inflation gases are essentially identical, reinforcing the fact that the difference between overall inflation pressure loss rates was the amount of pressurized oxygen available to permeate out (or react with the tire rubber).

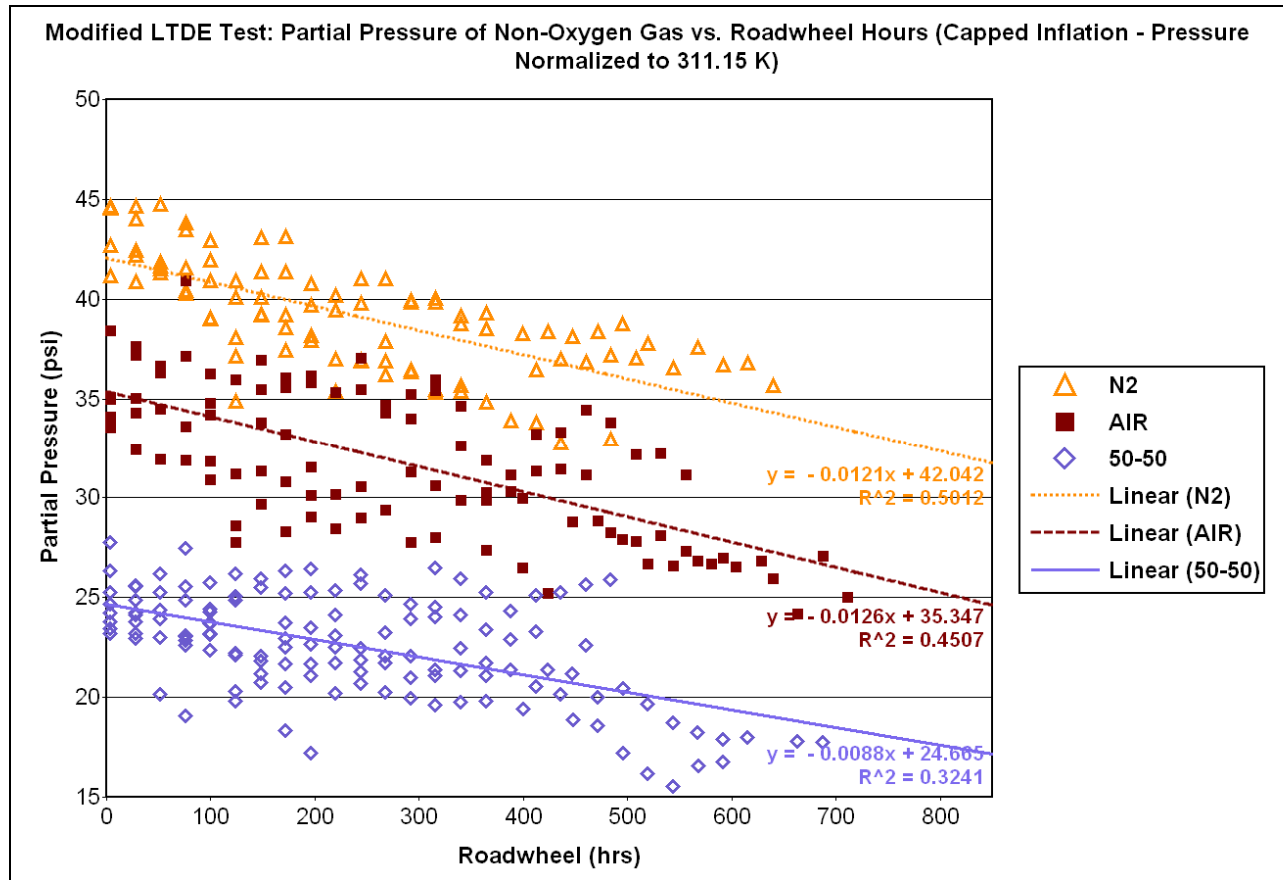


Figure 12. Changes in the Partial Pressure of Non-Oxygen Gas During Capped-Inflation Roadwheel Testing

The oxygen permeating through the tire is soluble in most of the tire rubber compounds and can react with internal tire components causing degradation even in small amounts. For instance, Hamed (2001) states that “A concentration of 1 to 2 percent of reacted oxygen is normally sufficient to cause severe deterioration in an elastomer”²¹ In Phase 1 of the Tire Aging Test Development Project, tires of six different models were retrieved from on-road service in Phoenix, Arizona, and sent for an analysis of material properties. Among the various material tests conducted was a measurement of the level of fixed oxygen in the skim rubber (at centerline of the rubber between the belts) and wedge rubber (rubber between the belt edges). These two components are in the belt-package region, which is the critical region for light vehicle radial tire durability. In Figure 13, the average levels of fixed oxygen in the skim and wedge rubber of tires collected in Phoenix after an average of 4 years of service (“Phase 1 - Phoenix”) are compared to the averages of new tires of the same models (“Phase 1 - New”).⁶ Additionally, in Figure 13 new tires of 10 of the tire models oven aged in Figure 6 of this report were subjected to the same oven aging procedures and sent for materials analysis (“Phase 4 - Oven...”) and compared to new versions of the same models (“Phase 4 - New”). As can be seen in the figure, the level of fixed oxygen absorbed by the internal belt-package rubber after an average of 4 years of service in Phoenix

⁶ Fixed oxygen results for “Phase 1 - Phoenix” tires are based on a total of 21 tires, representing six different tire models, with ages of 2.51 to 6.1 years old at the time of collection. “Phase 1 - New” tire results are based on 30 tires, representing the same six tire models, all purchased new.

increased approximately 0.5 percent when compared to new tires of the six new models. A similar increase can be seen in the ten new tire models oven aged for five weeks at 65° C (149° F) with the oxygen enriched 50/50 N₂/O₂ mixture.

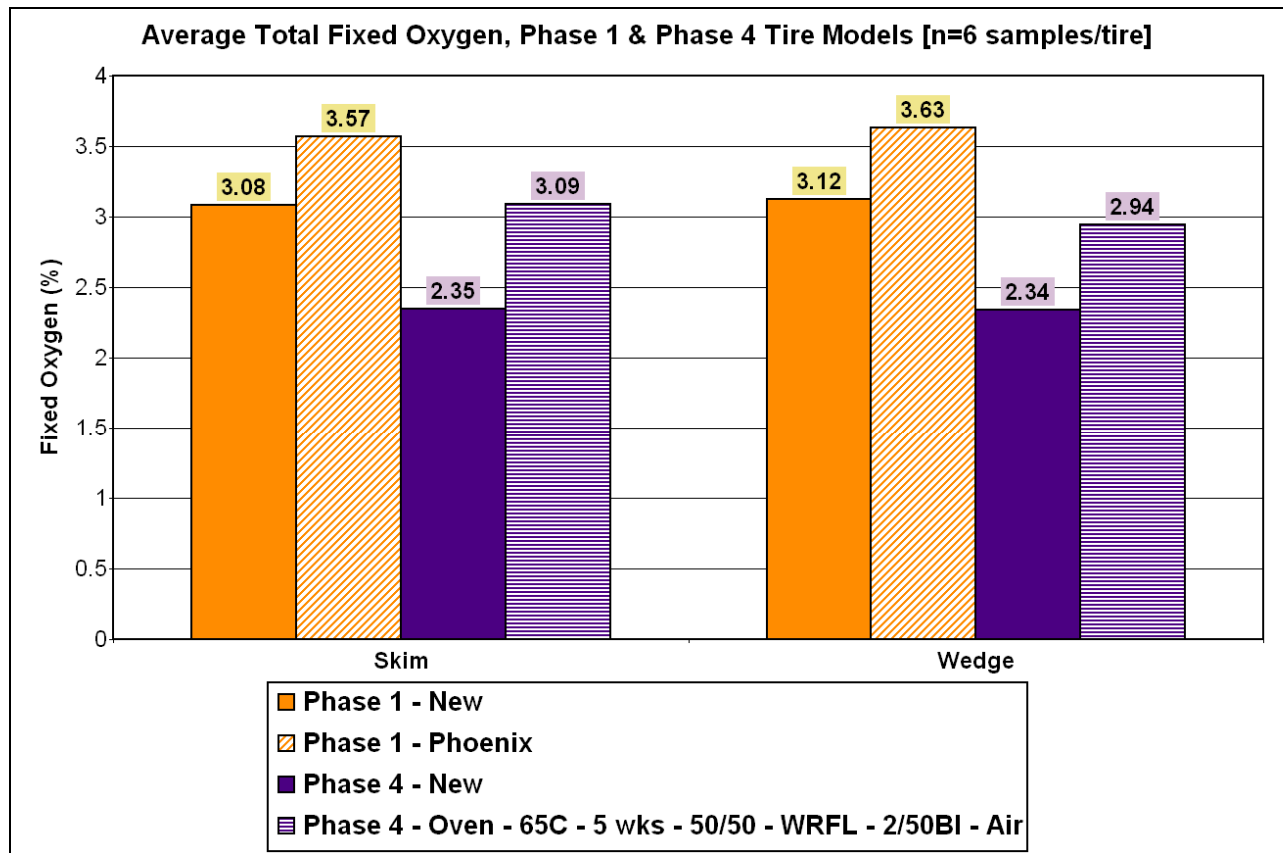


Figure 13. Changes in the Level of Fixed Oxygen in the Skim and Wedge Rubber Regions, New Tires, 5-Week Oven-aged Tires, Phoenix Tires

The oxygen that the internal tire rubber compounds absorbed or were exposed to during service in Phoenix resulted in a well documented thermo-oxidative reaction (i.e. involves heat and oxygen). At normal service temperatures this reaction is aerobic in passenger vehicle tires, meaning that oxygen participates in the reaction.^{19,23} The effects of this reaction on the wedge rubber between the steel-belt edges of the six tire models collected in Phoenix can be seen in the “Ahagon” plots in Figure 14. Data points for new tires start in the upper left corner of each plot and progress to the oldest tires in the lower right corner. Essentially, as the tires experience increasing lengths of service, the oxygen reacts with the rubber, making it harder (increased *100% Modulus*) and reducing the length the rubber will stretch before breaking (reduced *Extension Ratio at Break*), much like comparing new rubber bands to old ones. Researchers have determined that the normal aerobic oxidative reaction in passenger tires will yield a linear relationship when the log of the extension ratio is plotted against the log of the 100 percent modulus, with an empirically determined slope in the vicinity of -0.75 (referred to as “*Type 1 Aging*”).²³ The slopes for individual six tire models collected from Phoenix were linear, with slopes in the range of -0.64 to -0.92, indicating that these tires experienced aerobic “*Type 1 Aging*” during service in Phoenix.

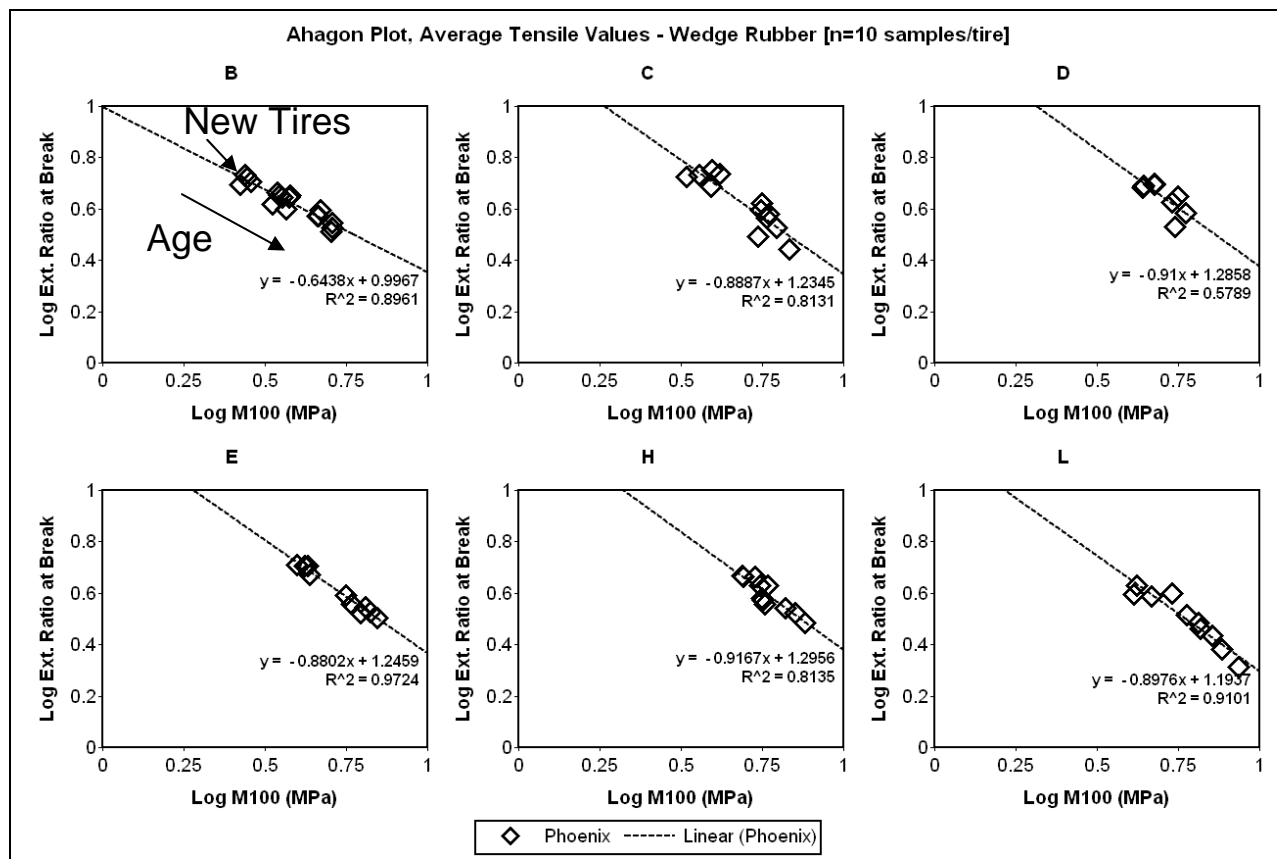


Figure 14. Changes in the Average Tensile Properties in the Wedge Rubber Region, New Tires and Phoenix Tires.

In Figure 15 the 10 new tire models in Phase 4 subjected to the 5-week oven aging procedure were plotted with the aggregate Phase 1 Phoenix tire tensile data. Despite being the fact that the Phase 4 models were different from the original 6 Phase 1 models, they followed the same “Type 1 Aging” trend in the wedge rubber between the belt edges. This indicates that the accelerated laboratory oven aging of the Phase 4 tires was also the aerobic “Type 1 Aging” seen in passenger cars during service.

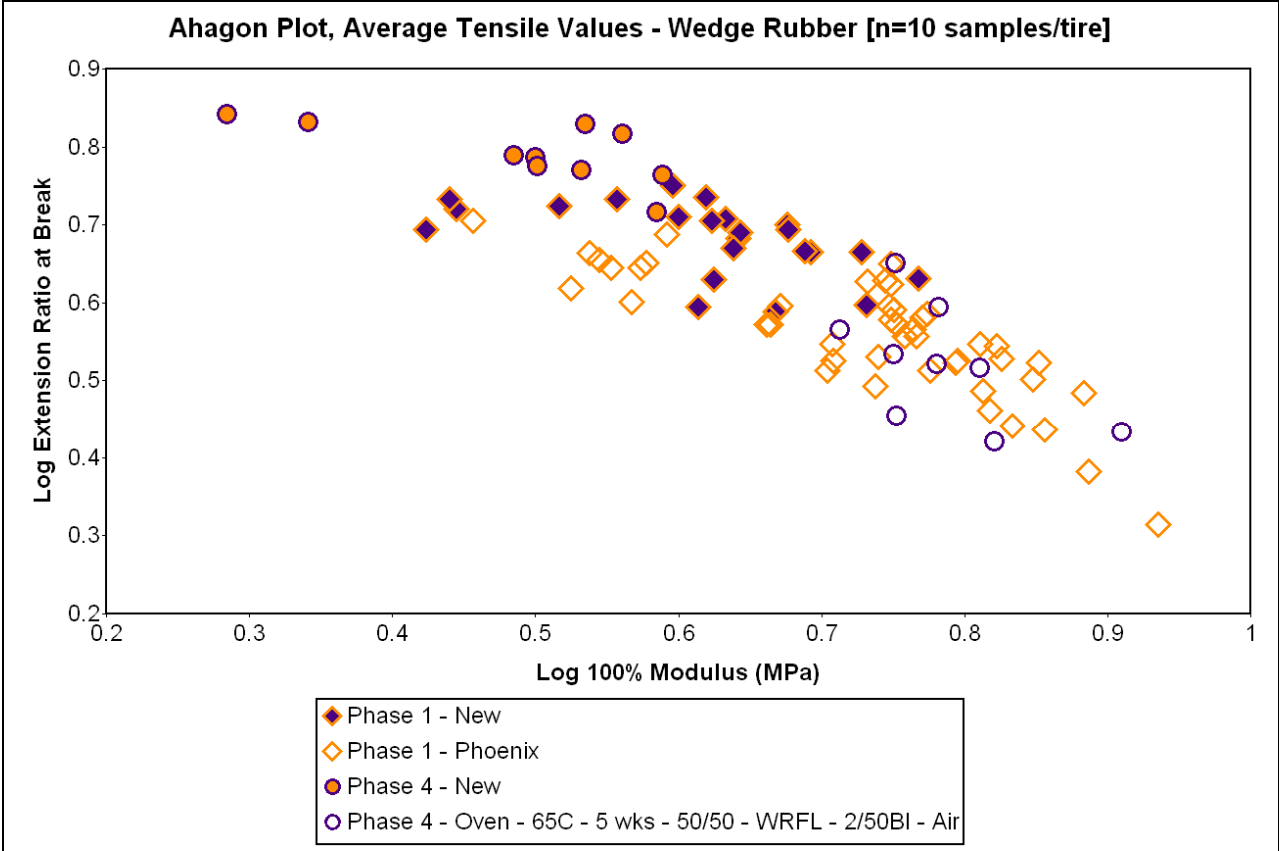


Figure 15. Changes in the Average Tensile Properties in the Wedge Rubber Region, New Tires, Phoenix Tires, and 5-Week Oven-Aged Tires

The effects of aerobic thermo-oxidative reaction on average inter-belt peel strength in the skim and wedge regions of the belt package can be seen in Figure 16. The average inter-belt peel strength in the skim and wedge rubber regions decreased approximately 21 to 28 lbf/in after an average of 4 years of service or following the 5-week oven aging process. This reduction in peel adhesion between the two steel belts can also be replicated by the laboratory oven aging procedure through acceleration of the oxidative process. It must be noted that this is a description of the average effects for property changes. The properties of individual tire components change at different rates depending on service and different tire types and constructions age at different rates.²⁴

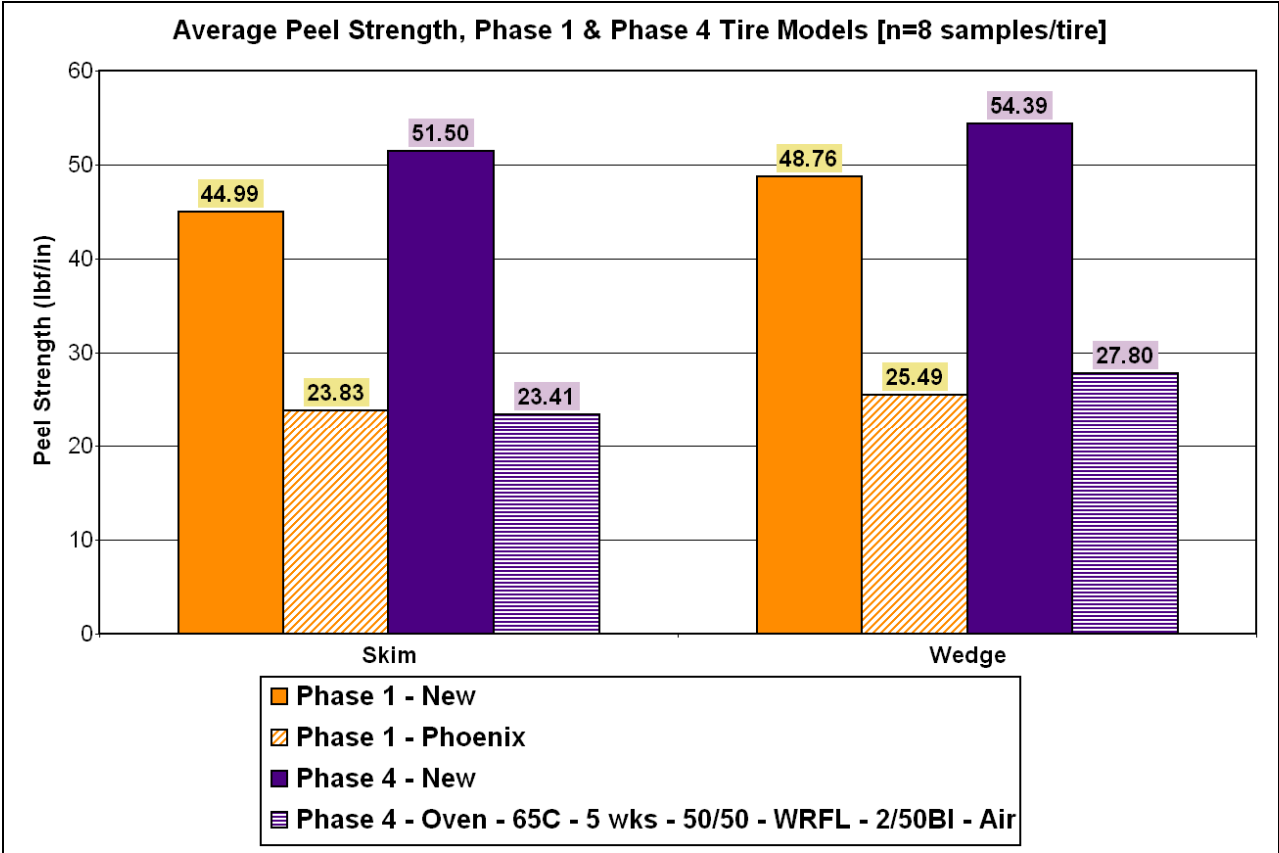


Figure 16. Changes in the Inter-Belt Peel Strength in the Skim and Wedge Rubber Regions, New Tires, Phoenix Tires, and 5-Week Oven-Aged Tires

In conclusion, the fixed oxygen results indicate that during normal on-road service in Phoenix a portion of the oxygen permeating through the tires was absorbed by the internal belt-package rubber compounds. The tensile properties from the Phoenix tires indicate that oxygen, in conjunction with the heat necessary for the reaction, produced aerobic thermo-oxidative degradation of the rubber between the two steel belts. One effect of the degradation of the belt-package rubber was to significantly reduce the tensile properties of the rubber between the two steel belts, a property that is critical to radial tire durability. These material properties changes in the rubber were reflected in the reduction in average peel adhesion between the two steel belts. Accelerated laboratory aging of the tires using a two-hour roadwheel break-in and 5 weeks of oven aging at 65° C, with an oxygen-enriched inflation gas, yielded changes in the level of absorbed oxygen, tensile properties, and peel strength properties in the internal belt package rubber that were similar to 4-year-old tires retrieved from service in Phoenix. Hence, out of 11 tire models that all successfully passed the FMVSS No. 139 Endurance and Low-Pressure tests when new, 3 models failed when oven aged prior to the FMVSS 139 roadwheel tests. These changes in material properties and roadwheel performance could be replicated in the laboratory through the use of elevated temperatures and oxygen-enriched inflation gas despite only running the tires 100 miles at 50 mph on the roadwheel during the break-in. Therefore the results strongly indicate that the degradative reaction of the internal tire rubber components is primarily a product of the internal pressurized oxygen and temperature conditions rather than purely mechanical fatigue of the tire

structure. Thus, inflating tires with nitrogen gas, thereby lowering the percentage of oxygen in the inflation gas, is one way to lessen the availability of oxygen to react with and degrade the internal components of the tire.

Summary:

Though the study was not specifically designed around evaluating the effects of nitrogen inflation, a sufficient number of tires with different inflation gases were tested in the various test programs to yield a number of statistically significant results. NHTSA testing of tires has confirmed that using nitrogen as an inflation gas in place of air slows the static IPL of the tire significantly. In the 90-day static room temperature test, the inflation pressure loss rate for tires inflated with nitrogen was approximately two-thirds of the loss rate of tires inflated with air. Dynamic testing on a roadwheel test shows the differences between the diffusion rate of air versus nitrogen versus 50/50 N₂/O₂ are maintained at higher temperatures and dynamic conditions (i.e., simulating rolling operation on a vehicle). The decrease in permeability for nitrogen gas was observed to be independent of tire innerliner composition and thickness, thus applicable to all tire types studied.

Inflating with nitrogen in place of air had little or no direct effect on tire rolling resistance performance. It should be noted that inflation with nitrogen merely slows the rate of diffusion of gas from the tire and is not a substitute for regularly maintaining tire pressure. Limited static inflation pressure loss rate testing with a 50/50 blend of nitrogen/oxygen inflation gas produced mixed results. The IPL for all tires began significantly higher, but dropped by the end of the 90-day test period to approximately the loss rate of air, which contains only 21 percent oxygen. Analysis of the gas content at the end of the test period confirmed that the rate of oxygen loss from the tire was approximately four times the rate of nitrogen loss averaged over the 90-day period. The reasons for the drop in IPL over time for the high-oxygen-content tires are unknown.

Seventy-six tires from 19 vehicles were measured for tire pressure and oxygen concentration. For the forty tires with the DOT code recorded, the average age of the tires at the time of inspection was 2.8 years with tires ranging for 0.6 to 6.8 years old. The average inflation pressure of the tires was 29.1 psi. The average percentage of oxygen measured in the inflation gas of field tires (on-vehicle tires) was 15.0 percent, and most values were significantly less than the original air inflation level of 20.9 percent. This suggests that the partial pressure of oxygen in the tire decreased significantly during service. Probably there are two contributing factors: first, oxygen has a higher permeation rate than nitrogen, and second, oxygen is consumed.

Using the estimate of 0.041 percent/month for each percentage reduction in O₂ percentage and the average IPL loss of 2.13 percent/month for the tires studied in the lab, the calculated IPL of these field tires would be reduced by approximately 11 percent (0.24%/month) due to the change in inflation gas composition. In other words, if a normally maintained in-service tire is not punctured or deflated, the faster diffusion/consumption of oxygen relative to the nitrogen content of the inflation gas results in an increase in the percentage of nitrogen gas from the original 78 percent to as high as the 91 percent observed, thus lowering the effective rate of inflation pressure loss. This means that the average loss rate for tires in the field may be considerably different than that measured using freshly inflated new tires. The benefits of nitrogen inflation on pressure retention of tires in service may be overstated by testing with new, freshly inflated tires in a labora-

tory test. Based on this study, the mean advantage in IPL for tires in service will be approximately 25 percent.

The results for 23 tires subjected to hundreds of hours of laboratory roadwheel aging with air, 50/50 N₂/O₂, or nitrogen inflation were inconclusive. Results did not indicate a correlation between the inflation gas used and the time to failure in this particular roadwheel durability test.

The results for 44 tires subjected to oven aging for 5-weeks at 65° C, followed by the 35.5 hour FMVSS No. 139 Endurance and Low Pressure test sequence, showed the oven and roadwheel test conditions to be sufficiently severe to differentiate between 50/50 N₂/O₂ inflation and the other two inflation gases, air and nitrogen. However, the oven and roadwheel test conditions were not severe enough to differentiate between air and nitrogen inflation. The oxygen concentration measurement data from both the accelerated dynamic roadwheel aging and static oven aging also showed a much more rapid diffusion/reaction of the oxygen portion of the inflation gas when compared to the nitrogen gas.

An analysis of common inter-belt rubber material properties from tires retrieved after an average of four years of on-vehicle service in Phoenix, Arizona demonstrated that a portion of the oxygen permeating through the tire is absorbed and reacts with the internal tire rubber compounds, which eventually leads to degradation of inter-belt adhesion. Accelerated laboratory aging of the tires using a two-hour roadwheel break-in and five weeks of oven aging at 65° C with an oxygen-enriched inflation gas yielded changes in the level of absorbed oxygen, tensile properties and peel strength properties in the internal belt package rubber that were similar to 4-year-old tires retrieved from service. Hence, out of 11 tire models that successfully passed the FMVSS No. 139 Endurance and Low Pressure tests when new, 3 models failed when oven aged prior to the roadwheel test. These changes in material properties and roadwheel performance could be replicated in the laboratory through the use of elevated temperatures and oxygen-enriched inflation gas despite only running the tires 100 miles at 50 mph on the roadwheel during the break-in. Therefore the results strongly indicate that the degradative reaction of the internal tire rubber components is a product of the internal pressurized oxygen and temperature conditions rather than from purely mechanical fatigue of the tire structure. Thus lowering the percentage of oxygen in the inflation gas may be one way to lessen the availability of oxygen to react with and degrade the internal components of the tire.

A primary positive result expected from nitrogen inflation may to produce more uniformly maintained tire pressure over time, which would help maintain tire performance properties such as handling, rolling resistance and durability. As seen from the effect of liner composition on IPL, this may be more important for some tire models. Also, there is a strong scientific basis for concluding that reducing the oxygen content of the inflation gas will reduce the internal thermo-oxidative degradation of the tire, which may aid in retention of durability.

References:

1. NHTSA. (July 26, 2001). *National Automotive Sampling System, Tire Pressure Special Study*. [PowerPoint slides]. Washington, DC: National Center for Statistics and Analysis, National Highway Traffic Safety Administration. Retrieved from <http://www-nrd.nhtsa.dot.gov/pdf/nrd-01/NRDmtgs/2001/0701TirePressure.pdf>
2. Rubber Manufacturers Association. (2006). *Tire Information Service Bulletin TISB Vol. 44, No. 1, Using Nitrogen to Inflate Passenger and Light Truck Tires in Normal Service Applications*. Washington, DC.
3. Nitrogen Direct. (2005). <http://www.nitrogendirect.com/N2Info.htm>
4. Sabino, L. (2000). Degree thesis, University of Bologna, Mechanical Engineering Department, 2000. *Abstract, Chapters: III and IV. Tyres Inflation with De-Oxygenated [sic] Air*. Bologna, Italy: University of Bologna.
5. Sperberg, L. R. (1967). Tire Durability with Nitrogen Inflation. *Rubber Age* **99** (11), 83
6. Sperberg, L. R. (1985). Stronger Longer Tires of El Paso, Million Mile Truck Tires – Available Today: One of the World’s Best Kept Secrets.
7. Tokita, N., Sigworth, W. D., Nybakkan G. H., & Ouyang G. B. (1985). Long Term Durability of Tires. *Proceedings of the International Rubber Conference, Kyoto, Japan*. p 672.
8. Walenga, G. (2004). Nitrogen Inflation for Truck Tires. *Clemson Tire Conference*. Clemson University.
9. Fisher, P. (July 17, 2000). A New Gas for the New Millennium? *Tire Business*.
10. Bridgestone Firestone North American Tire, LLC. (2003). Vol. 8, Issue 3, *Should You Stop Putting Air in Your Tires? Real Questions, Real Answers*.
11. Petersen, G. (October 4, 2007). *Tires - Nitrogen air loss study*. Consumer Reports Blog, Cars. <http://blogs.consumerreports.org/cars/2007/10/tires-nitrogen-.html>.
12. ExxonMobil Chemical. (August 28, 2006). *Nitrogen Inflation of Tires*. [PowerPoint slides]. Docket Document ID: NHTSA-2005-21276-23, Federal Docket Management System at <http://www.regulations.gov>.
13. National Research Council of the National Academies. (2006). Transportation Research Board Special Report 286: Tires and Passenger Vehicle Fuel Economy. Washington, DC: The National Research Council. http://www.nap.edu/catalog.php?record_id=11620.
14. National Highway Traffic Safety Administration. (2007). *Research Report to Congress on Tire Aging, DOT HS 810 799*. Docket Document ID: NHTSA-2005-21276-42, Federal Docket Management System at <http://www.regulations.gov>.
15. Baldwin, J. M., Bauer, D. R., & Ellwood, K. R. (2004). Effects of Nitrogen Inflation on Tire Aging and Performance. *Rubber & Plastics News, Vol. 34, No. 4*, 14-19.
16. ASTM International, F09.30 Aged Tire Durability Task Group. (2007, July 24). *Status Update, NHTSA Briefing*. PowerPoint slides. Docket Document ID: NHTSA-2005-21276-41, Federal Docket Management System at <http://www.regulations.gov>.
17. Ahagon, A., Kida, M., & Kaidou, H. (1990). *Rubb. Chem. Technol.*, **63**, 683
18. Cohen, M. (2004). *How Tires Age and How to Characterize Aging in Tires*. PowerPoint slides. International Tire Exhibition and Conference.
19. Bauer, D. R., Baldwin, J. M., & Ellwood, K. R. (2005). Correlation of Rubber Properties between Field Aged Tires and Laboratory Aged Tires. *Rubb. Chem. Technol.*, **78**, 777.

- Docket Document ID: NHTSA-2005-21276-11, Federal Docket Management System at <http://www.regulations.gov>.
20. Evans, L. R., Feve, S., & MacIsaac, J. D. (2007). *Evaluation of New and Aged Tires by Accelerated Service Life Tests: Comparison Using a Stepped-Up-Load and a Stepped-Up-Speed Roadwheel Test*. [PowerPoint slides]. The Tire Society Conference.
 21. Gent, A. N. (Ed.). (2001). *Engineering with Rubber, 2nd Edition*. Hamed, G. R., Chapter 2, Materials and Compounds, p. 26. Cincinnati, OH: HanserGardner Publications, Inc.
 22. NHTSA. (2005). Docket: NHTSA-2005-21276-1, Federal Docket Management System at <http://www.regulations.gov>.
 23. Kaidou, H., & Ahagon, A. (1990). *Rubb. Chem. Technol.*, **63**, 698
 24. Shelton, J. R. (1957). *Rubb. Chem. Technol.*, **30**, 1251

Acknowledgements:

The authors wish to thank James A. Popio, Ph.D., of Smithers Scientific Services, Inc., for valuable technical contributions.

Project support services and testing was performed by:

Akron Rubber Development Laboratory, Inc.
2887 Gilchrist Rd.
Akron, Ohio 44305

Smithers Scientific Services, Inc.
1150 North Freedom Street
Ravenna, Ohio 44266

Standard Testing Laboratories
1845 Harsh Avenue SE.
Massillon, Ohio 44648

Transportation Research Center, Inc.
P.O. Box B-67
10820 State Route 347
East Liberty, Ohio 43319

Appendix A: Tire Types

Tire Type	Manufacturer	Brand Name	Tire Model	Tread Design	Size	Load Range	Speed Rating	Tread Wear Grade	Traction Grade	Temp. Grade	Avg. Weight (lbs)
B	Michelin	BFGoodrich	Touring T/A SR4	All Season	P195/65R15	089	S	540	A	B	-
B1	Bridgestone	Bridgestone	Blizzak DM-Z3	Winter	235/75R16	105	Q	-	-	-	31.37
B7	Bridgestone	Firestone	Wilderness AT I	All Season	P265/75R16	114	S	440	B	B	40.76
B8	Bridgestone	Bridgestone	B450	All Season	P205/65R15	092	S	360	B	B	19.95
B9	Bridgestone	Bridgestone	Duravis M773 II	All Season	LT265/75R16	123 (E)	-	-	-	-	48
C	Goodyear	Goodyear	Eagle GA	All Season	P205/65R15	092	V	300	A	A	-
C7	Continental	Continental	Contitrac TR	All Season	P265/70R17	113	S	520	A	B	40.93
C8	Continental	General	Ameri G4S	All Season	P205/65R15	092	T	520	A	B	20.31
D	Michelin	Michelin	LTX M/S	All Season	P235/75R15XL	108	S	440	A	B	-
D6	Goodyear	Mohave [Discount Tire]	RS	All Season	P205/65R15	092	R	360	A	B	19.11
D7	Cooper	Cooper	Discoverer ST-C	All Season	LT235/85R16	120 (E)	N	-	-	-	44.42
D8	Cooper	Cooper	Discoverer ST-C	All Season	LT245/75R16	120 (E)	N	-	-	-	44.85
E	Bridgestone	Firestone	Wilderness AT I	All Season	P265/75R16	114	S	440	B	B	-
G1	Goodyear	Goodyear	Ultra Grip	Winter	P235/75R15XL	108	S	-	-	-	32.62
G11	Goodyear	Goodyear	Integrity	All Season	P225/60R17	098	S	460	A	B	24.46
G8	Goodyear	Goodyear	Integrity	All Season	225/60R16	098	S	460	A	B	22.9
H	Goodyear	Pathfinder [Discount Tire]	ATR A/S	All Season	LT245/75R16	120 (E)	Q	-	-	-	-
H3	Hankook	Hankook	DynaPro AS	All Season	LT245/75R16	120 (E)	-	-	-	-	42.91
L	Continental	General	Grabber ST	All Season	255/65R16	109	H	360	B	A	31.9
M1	Michelin	Michelin	Cross Terrain SUV	All Season	P265/75R16	114	S	700	A	B	39.13

Tire Type	Manufacturer	Brand Name	Tire Model	Tread Design	Size	Load Range	Speed Rating	Tread Wear Grade	Traction Grade	Temp. Grade	Avg. Weight (lbs)
M10	Michelin	Michelin	LTX A/S	All Season	LT245/75R16	120 (E)	R	-	-	-	43.51
M3	Michelin	Michelin	X-Ice	Winter	205/65R15	094	Q	-	-	-	21.66
N1	Cooper	Nokian	Hakkapeliitta 10LT	Winter	LT235/85R16	120 (E)	-	-	-	-	41.97
N2	Nokian	Nokian	Hakkapeliitta LT	Winter	LT265/75R16	119 (D)	-	-	-	-	46.69
O4	Cooper	Big O [Big O Tire]	X/T BIG FOOT (356)	All Season	LT265/75R16	123 (E)	N	-	-	-	49.79
P3	Cooper	Futura [Pep Boys]	Scrambler A/P (P-XL)	All Season	P235/75R15XL	108	S	400	A	B	31.75
S1	Sumitomo	Sumitomo	HTR+	All Season	225/60R16	098	V	400	AA	A	25.11
T2	Toyo	Toyo	800 Ultra	All Season	P235/60R16	099	T	700	A	B	27.3
U2	Goodyear	Dunlop	SP Sport 4000 DSST (Run Flat)	Run_Flat	P225/60R17	098	T	360	A	B	35.25
Y2	Yokohama	Yokohama	Geolandar A/T+II	All Season	LT285/75R16	122 (D)	Q	-	-	-	58.31

Appendix B: Modified LTDE Test Procedures with Alternate Inflation Gases

The Michelin Long Term Durability Endurance (LTDE) roadwheel testing parameters are contained in Table 13:

Table 13. LTDE Test Parameters

Parameter	P-Metric/Metric		Light Truck
	Standard Load	Extra Load	E
Load Range			
Test Temp	38°C ±3°C (100°F ±5°F)		
Speed	97 km/h (60 mph)		
Filling Gas	As Specified*		
Load (% max single)	111		92
Initial Pressure	276 kPa (40 psi)	317 kPa (46 psi)	552 kPa (80 psi)

*Inflation pressure during these tests was capped rather than topped off every 24 hours as is done in the standard LTDE test procedure.

Tires should be tested according to the following instructions:

- Conduct pre-test shearography.
- The tires should be mounted according to inflation mixture instructions and an Item 50 new metal valve stem should be used for each test.
- The tire shall be filled with the specified inflation mixture (air, nitrogen, or 50/50 N₂/O₂). Statically condition the tire for no less than 24 hours at 38 ±3 °C. On the day of testing: Check, readjust inflation pressure if necessary to test specified pressure, and recap the tire valve. Measure initial percent O₂ in the inflation gas immediately before commencing testing.
- All tests shall be conducted on a 1.707 m (67.23 in) roadwheel per specifications with the string limits set 2.0" ±0.5" from the surface of the tire.
- If the test must be interrupted while in progress (due to maintenance or calibration), cap and store the tires in a cool (<77° F) environment until test is restarted.
- After the first 4 hours of running time, stop the test and allow at least 15 minutes to pass before entering the roadwheel enclosure. Then measure record inflation pressure and percent O₂ concentration.
- Stop test every 24 hours thereafter. Allow at least 15 minutes to pass before entering the roadwheel enclosure. Then measure and record inflation pressure and percent O₂ concentration.
- Tires shall be run until catastrophic tire failure.
- After the failure occurs: Allow at least 15 minutes after the test is completed before entering the roadwheel enclosure. If safe and the tire is still inflated, measure and record the final pressure and percent O₂ concentration within 1 hour of the end of the test. Deflate and unmount the tire and then conduct the post-test tire inspection. Include the time and the equivalent mileage at which the failure occurred in report, and then take the three specified photographs.

Appendix C: Oven-Aging Test Protocol

Table 14. Oven-Aging Test Parameters

Task Name	Time (weeks)	Temp (C)	Oven Aging Inflation Gas	Test Pressure	Pre-Oven Road-wheel Break-In (hrs)	Inflation Gas Replacement
HYB5_65_IV_BI_2_R	5	65 ±3°	50/50 N ₂ /O ₂ ±2% (Certified Mix)	100% max sw load pressure*	2	Weekly
HYB5_65_IV_BI_2_R_AIR	5	65 ±3°	Shop Air	100% max sw load pressure*	2	Weekly
HYB5_65_IV_BI_2_R_N2	5	65 ±3°	Nitrogen (> 99% purity)	100% max sw load pressure*	2	Weekly

*The pressure that corresponds to the max sidewall load per the tables used to certify the tire (i.e. T&RA, ETRTO, JATMA, etc.)

General Test Parameters

▪ Conditioning (All Tires)

- Remove all tags, stickers, tape, stones and other foreign objects from tires.
- Mount tires with normal shop air per normal safety protocols.
- Condition the tire for not less than three hours at 38 +0, -6 degrees C (100 +0, -10) prior to testing.

▪ 2-Hour Roadwheel Break-In

- Procedure is exactly the FMVSS No. 139 High Speed test break-in.
- The tire is conditioned pre-test as above.
- Mark the direction of rotation on the test tires.
- Inflation gas: Air.
- *Preparation of tire.*
 - Mount the tire on a test rim and inflate it to the pressure specified for the tire in the following table:

Tire Application	Test Pressure (kPa)
P-Metric: Standard load	220
Extra load	260
Load Range C	320
Load Range D	410
Load Range E	500

- Before or after mounting the assembly on a test axle, readjust the tire pressure to the level previously specified
- *Test procedure*

- Press the assembly against the outer face of a test drum with a diameter of 1.70 m.
- Apply to the test axle a load equal to 85 percent of the tire's maximum load carrying capacity.
- Break-in the tire by running it for 2 hours at 80 km/h.

General Oven-Aging Test Procedures



- Mount each test tire per instructions and use a new metal valve stem. When using the 50/50 mix, observe all specified safety precautions, especially: *"The tire is seated with normal air instead of the 50/50 mixture, and then vented to 0 psig before inflation with the 50/50 mixture."*
- Condition the tire for at least three hours at 38 +0, -6 degrees C (100 +0, -10) prior to testing.
- Age tire in an air-circulating oven per specified oven-aging parameters with either spacers between each wheel, on racks, or suspended so as no tire is subject to the additional weight of more than one tire above it. Allow sufficient room for adequate air flow around each tire.
- **Inflation Gas Replacement**
 - Conducted weekly
 - Remove tire from oven and allow to cool at 38 +0, -6 degrees C (100 +0, -10) for at least one hour
 - Measure and record the pressure and percent O₂ concentration in the inflation gas (unit must be accurate to ±0.1%)
 - Inspect general condition of tire, paying special attention to valve stem and bead areas
 - If tire condition is acceptable, remove valve stem core and allow to deflate to atmospheric pressure
 - Re-install valve stem core and inflate to test pressure with fresh inflation mixture
 - Return tire to the oven for aging as soon as it is practicable; document time tire entered oven
- Once the oven aging period is complete, remove the tire from the oven and allow to cool at 38 +0, -6 degrees C (100 +0, -10) for at least one hour before measuring and recording the pressure and percent O₂ concentration in the inflation gas.
- If the tire passes inspection, send it on to the designated post oven aging testing.

Appendix D. FMVSS Title 49. Transportation Part 571.139 Standard No.139 (10-01-04); New pneumatic radial tire for light vehicles. See the standard for details. Test procedures used for testing to requirements of FMVSS No 139, Section S6.3 Endurance and S6.4 Low Inflation Pressure Performance specifies test conditions used for this study.

The test conditions for Section 6.3 (endurance) are:

Passenger Car Tires	
Standard Load	180 kPa
Extra Load	220 kPa
Light Truck (LT)	
LR C	260 kPa
LR D	340 kPa
LR E	410 kPa
Temperature	38°C
Speed	120 km/h

Load	85% for 4 hours
	90% for 6 hours
	100% for 24 hours

- Remove all tags, stickers, tape, stones and other foreign objects from tires
 - Mount the tire on a test rim and inflate it to the pressure specified for the tire in the above table
 - Condition the tire for not less than three hours at 38 +0, -6 degrees C (100 +0, -10) prior to testing
 - Before or after mounting the assembly on a test axle, readjust the tire pressure to the level previously specified
- *Test procedure*
- Press the assembly against the outer face of a road-wheel with a diameter of 1.70 m at above speed.
 - Apply to the test axle a load per equal to specified percentage of tire's maximum load carrying capacity.
 - Continue for the required period of time and adjust load per schedule.
 - After allowing to cool, inspect tire, take and record posttest pressure, and proceed to Section 6.4 Low Pressure (LP).

The test conditions for Section 6.4 Low Pressure (LP) are:

Passenger Car Tires Pressures	
Standard Load	140 kPa
Extra Load	160 kPa

Light Truck (LT)		
	LR C	200 kPa
	LR D	260 kPa
	LR E	320 kPa
Temperature		38°C
Speed		120 km/h

Load	100% for 1.5 hours
------	--------------------

- After completion of the endurance test, deflate the tire to the pressure specified for that tire in the above table.
- Condition the tire for not less than three hours at 38 +0, -6 degrees C (100 +0, -10) prior to testing.
- Before or after mounting the assembly on a test axle, readjust the tire pressure to the level previously specified.

▪ *Test procedure*

- Press the assembly against the outer face of a road-wheel with a diameter of 1.70 m at above speed.
- Apply to the test axle a load per equal to 100 percent of tire's maximum load carrying capacity.
- Continue for the required period of time.

DOT HS 811 094
March 2009



U.S. Department
of Transportation
**National Highway
Traffic Safety
Administration**

★★★★★
NHTSA

www.nhtsa.gov